

First principles study of helium, carbon and nitrogen in austenite, dilute austenitic iron alloys and nickel.

D.J. Hepburn,* D. Ferguson, S. Gardner, and G.J. Ackland†
*Institute for Condensed Matter and Complex Systems, School of Physics and SUPA,
 The University of Edinburgh, Mayfield Road, Edinburgh, EH9 3JZ, UK.*
 (Dated: January 24, 2013)

An extensive set of first-principles density functional theory calculations have been performed to study the behaviour of He, C and N solutes in austenite, dilute Fe-Cr-Ni austenitic alloys and Ni in order to investigate their influence on the microstructural evolution of austenitic steel alloys under irradiation. The results show that austenite behaves much like other fcc metals and like Ni in particular. Strong similarities were also observed between austenite and ferrite. We find that interstitial He is most stable in the tetrahedral site and migrates with a low barrier energy of between 0.1 and 0.2 eV. It binds strongly into clusters as well as overcoordinated lattice defects and forms highly stable He-vacancy ($V_m\text{He}_n$) clusters. Interstitial He clusters of sufficient size were shown to be unstable to self-interstitial emission and $V\text{He}_n$ cluster formation. The binding of additional He and V to existing $V_m\text{He}_n$ clusters increases with cluster size, leading to unbounded growth and He bubble formation. Clusters with n/m around 1.3 were found to be most stable with a dissociation energy of 2.8 eV for He and V release. Substitutional He migrates via the dissociative mechanism in a thermal vacancy population but can migrate via the vacancy mechanism in irradiated environments as a stable $V_2\text{He}$ complex. Both C and N are most stable octahedrally and exhibit migration energies in the range from 1.3 to 1.6 eV. Interactions between pairs of these solutes are either repulsive or negligible. A vacancy can stably bind up to two C or N atoms with binding energies per solute atom up to 0.4 eV for C and up to 0.6 eV for N. Calculations in Ni, however, show that this may not result in vacancy trapping as VC and VN complexes can migrate cooperatively with barrier energies comparable to the isolated vacancy. This should also lead to enhanced C and N mobility in irradiated materials and may result in solute segregation to defect sinks. Binding to larger vacancy clusters is most stable near their surface and increases with cluster size. A binding energy of 0.1 eV was observed for both C and N to a [001] self-interstitial dumbbell and is likely to increase with cluster size. On this basis, we would expect that, once mobile, Cottrell atmospheres of C and N will develop around dislocations and grain boundaries in austenitic steel alloys.

PACS numbers: 61.72.-y, 61.82.Bg, 71.15.Mb, 75.50.Bb, 75.50.Cc, 75.50.Ee

I. INTRODUCTION

Steel, in its many forms, is the primary structural material in current fission and fusion systems and will be so for the foreseeable future. Carbon (C) and nitrogen (N) are both commonly found in steel, either as important minor alloying elements or as low concentration impurities. In body centred cubic (bcc) α -iron (α -Fe), it has been shown experimentally that C interacts strongly with vacancy point defects and more weakly with self-interstitial defects^{1,2} and can form so called Cottrell atmospheres around dislocations³, influencing yield properties and leading to strain ageing of the material. First principles (ab initio) calculations, as summarised in a recent review by Becquart and Domain⁴, support these findings and demonstrate that N exhibits similarly strong interactions. As such, both of these elements have a significant influence on microstructural evolution in bcc Fe, even down to very low concentrations, and a detailed understanding of their interactions and dynamics in steels is worthy of development, more generally.

Helium (He) is produced in significant quantities in the high neutron-irradiation fluxes typically experienced by the internal components of fission reactors and in the structural materials for fusion systems by (n, α) transmu-

tation reactions. In combination with the primary point defect damage typical of irradiated environments, the presence of He plays a critical role in the microstructural evolution of these materials. As a result of its low solubility in metals, He becomes trapped in regions of excess volume, such as dislocations, grain boundaries and, most strongly, in vacancies and vacancy clusters⁵⁻¹². As such, it aids the nucleation, stabilisation and growth of voids (He bubbles), resulting in swelling of the material^{10,13-16}. The formation of He bubbles has also been implicated in high-temperature embrittlement of materials^{10,17,18}. It is therefore of critical importance to gain a deep understanding of the behaviour of He in these materials and the part it plays in the underlying mechanisms of microstructural evolution.

First principles electronic structure calculations offer the most accurate means to develop an atomic level understanding of the dynamics and interactions of solutes and point defects in solids. As such, they play a central role in the development of a theoretical understanding of the microstructural evolution of irradiated materials, as part of a multi-scale modelling approach, such as that used in the FP6 project, PERFECT¹⁹ and the FP7 project, PERFORM60²⁰.

The behaviour and interactions of He in a num-

ber of bcc and face-centred cubic (fcc) metals have been studied using density functional theory (DFT) techniques^{4,19,21–30}. This database of He kinetics and interactions is essential for the interpretation of complex experimental results, such as those present in thermal He desorption spectra. A case in point is the work of Ortiz *et al.*³¹, who have developed a rate theory model based on DFT calculations of the kinetics and interactions of point defects, He and C in bcc Fe^{25,31,32}. The model successfully reproduces and interprets the existing experimental desorption results⁸. It is interesting to note that agreement with experiment was only possible once the effects of C were included, even though only 150 at. ppm of C was necessary; this again indicates the sensitivity of the microstructural evolution to C concentration. To date, however, there have been no ab initio studies of He in austenite, that is fcc γ -Fe, or austenitic FeCrNi alloys. This, primarily, is a result of the difficulty in describing the paramagnetic state of these materials.

Ab initio calculations have also been used to extensively study C^{4,31,33–37} and N^{4,34} in bcc Fe. These calculations show excellent agreement with experimentally verifiable parameters, such as the migration energy barrier for C diffusion, where ab initio values of 0.86 eV^{33,36}, 0.87 eV³⁷ and 0.90 eV³⁴ are in good agreement with the experimental value of 0.87 eV^{2,38}. For N, an equally good agreement is seen for the migration barrier, where a value of 0.76 eV was found by ab initio calculations³⁴ and a value of 0.78 eV was found experimentally³⁹. Calculations in austenite are, however, limited primarily to solute dissolution, diffusion and their influence on the electronic structure and local geometry^{33,40–42} although calculations of vacancy-C binding have been performed⁴³.

In this work we present a detailed study of the energetics, kinetics and interactions of He, C and N solutes in model austenite and austenitic systems using DFT. A full treatment of paramagnetic austenite and FeCrNi austenitic alloys would naturally take into account the magnetic and composition dependence of the variables under study and while ab initio techniques are now becoming available to model the paramagnetic state⁴⁴ and calculations in concentrated alloys are certainly achievable⁴⁶, their complexity precludes a broad study of all the necessary variables relevant for radiation damage modelling. Previous studies have, instead, either taken ferromagnetic (fm) fcc nickel (Ni) as a model austenitic system^{19,22,47} or modelled austenite using a small set of stable, magnetically ordered states, as in our previous work⁴⁸. The advantage is that a more detailed study is possible, but the level of approximation involved is certainly not ideal and careful use should be made of the results obtained. Here, we follow the same approach used in our previous work⁴⁸, performing our calculations in the two most stable ordered magnetic states of fcc Fe. In addition, we present and compare the results of corresponding calculations in fm Ni in order to make more general conclusions in Fe-Ni based austenitic alloys.

In section II we present the details of our calculations.

We then proceed to present and discuss our results for He, C and N solutes in defect free austenite and dilute Fe-Cr-Ni austenitic alloys in section III and their interactions with point defects and small vacancy clusters in section IV before making our conclusions.

II. COMPUTATIONAL DETAILS

The calculations presented in this paper have been performed using the plane wave DFT code, VASP^{49,50}, in the generalised gradient approximation with exchange and correlation described by the parametrisation of Perdew and Wang⁵¹ and spin interpolation of the correlation potential provided by the improved Vosko-Wilk-Nusair scheme⁵². Standard projector augmented wave potentials^{53,54} supplied with VASP were used for Fe, He, C, N, Ni and Cr with 8, 2, 4, 5, 10 and 6 valence electrons respectively. First order ($N = 1$) Methfessel and Paxton smearing⁵⁵ of the Fermi surface was used throughout with the smearing width, σ , set to 0.2 eV to ensure that the error in the extrapolated energy of the system was less than 1 meV per atom. A 2^3 k-point Monkhorst-Pack grid was used to sample the Brillouin zone and a plane wave cutoff of 450 eV.

All calculations used supercells of 256 ($\pm 1, \pm 2, \dots$) atoms, with supercell dimensions held fixed at their equilibrium values and ionic positions free to relax. For the relaxation of single configurations, structures were deemed relaxed once the forces on all atoms had fallen below 0.01 eV/Å. For the nudged elastic band⁵⁶ (NEB) calculations used to determine migration barriers an energy tolerance of 1 meV or better was used to control convergence. Spin-polarised calculations have been performed throughout this work with local magnetic moments on atoms initialised to impose the magnetic state ordering but free to relax during the calculation. The relaxed local magnetic moments were determined by integrating the spin density within spheres centred on the atoms. Sphere radii of 1.302, 0.635, 0.863, 0.741, 1.286 and 1.323 Å were used for Fe, He, C, N, Ni and Cr respectively.

We have performed our calculations in both the face centred tetragonal (fct) antiferromagnetic single layer (afmI) and double layer (afmD) collinear magnetic reference states for austenitic Fe (at $T=0$ K), which we will refer to as afmD Fe and afmI Fe in what follows, respectively, using the same methodology as our previous work⁴⁸. Both of these structures consist of (ferro-)magnetic (001) fcc planes, which we will refer to as magnetic planes in what follows, but with opposite magnetic moments on adjacent planes in the afmI state and an up,up,down,down ordering of moments in adjacent magnetic planes in the afmD state. The fcc fm and fct fm states were found to be structurally unstable and spontaneously transformed upon addition of a whole range of defects and solutes⁴⁸. The fcc ferromagnetic high-spin (fm-HS) state was, however, found to be stable to

isotropic effects and we have performed a select few calculations in this state for comparison with other work in the literature³³. We have also performed a number of calculations in fcc fm Ni, which we will refer to, simply, as Ni in what follows, where these results were not available in the literature. We take the lattice parameters for afmI Fe as $a = 3.423$ Å and $c = 3.658$ Å, those for afmD Fe as $a = 3.447$ Å and $c = 3.750$ Å and take $a = 3.631$ Å for fm-HS Fe. Calculations in Ni have been performed with an equilibrium lattice parameter of $a = 3.522$ Å. The corresponding magnitudes for the local magnetic moments in bulk, equilibrium afmI, afmD and fm-HS Fe were determined as 1.50, 1.99 and 2.57 μ_B , respectively⁴⁸ and a local moment of 0.59 μ_B was found in bulk, equilibrium Ni. Convergence tests indicated that local moments were determined to a few hundredths of μ_B .

We use elastic constants for our reference states, as determined previously⁴⁸, or determined here using the same techniques. For fm-HS Fe, we find $C_{11} = 40$ GPa, $C_{12} = 240$ GPa and $C_{44} = -10$ GPa, which clearly shows instability to shear strains and tetragonal deformations, as $C' = C_{11} - C_{12} = -200$ GPa. It is, however, stable to isotropic deformations as the bulk modulus, $B = 187$ GPa, is positive. For Ni, we find $C_{11} = 272$ GPa, $C_{12} = 158$ GPa and $C_{44} = 124$ GPa, which gives $C' = 114$ GPa and $B = 196$ GPa, and shows that this material is stable to any strain deformations.

We have determined the solution enthalpy for carbon in Fe and Ni using diamond as a reference state. The diamond structure was determined using the same settings as our other calculations but with sufficient k-point sampling to ensure absolute convergence of the energy. We found a lattice parameter of $a = 3.573$ Å, in good agreement with the standard experimental value.

We define the formation energy, E_f , of a configuration containing n_X atoms of each element, X, relative to a set of reference states for each element using

$$E_f = E - \sum_X n_X E_X^{\text{ref}}, \quad (1)$$

where E is the calculated energy of the configuration and E_X^{ref} is the reference state energy for element, X. We take the reference energies for Fe, Ni and Cr to be the energies per atom in the bulk metal, that is Fe in either the afmI, afmD or fm-HS states, as appropriate, Ni in its fcc fm ground state and Cr in its bcc antiferromagnetic (afm) ground state. Details of the Fe and Ni reference states are given above, whereas for Cr an equilibrium lattice parameter of 2.848 Å was found with a corresponding local moment of magnitude 0.87 μ_B . For He, C and N the reference states were taken to be the non-magnetic free atom, as calculated in VASP.

In a similar manner, we define the formation volume at zero pressure, V_f , of a configuration relative to the bulk metal by

$$V_f = V(0) - n_{\text{bulk}} V_{\text{bulk}}, \quad (2)$$

where $V(0)$ is the volume of the configuration at zero pressure, n_{bulk} is the number of bulk (solvent) metal atoms in the configuration and V_{bulk} is the volume per atom in the defect-free bulk metal, which we found to be 11.138, 10.712, 11.970 and 10.918 Å³ in afmD Fe, afmI Fe, fm-HS Fe and Ni, respectively. For our calculations, $V(0)$ was determined by extrapolation from our calculations at the fixed equilibrium volume using the residual pressure on the supercell and the bulk modulus for the defect-free metal.

We define the binding energy between a set of n species, $\{A_i\}$, where a species can be a defect, solute, clusters of defects and solutes etc., as

$$E_b(A_1, \dots, A_n) = \sum_{i=1}^n E_f(A_i) - E_f(A_1, \dots, A_n) \quad (3)$$

where $E_f(A_i)$ is the formation energy of a configuration containing the single species, A_i , and $E_f(A_1, \dots, A_n)$ is the formation energy of a configuration containing all of the species. With this definition an attractive interaction will correspond to a positive binding energy. One intuitive consequence of this definition is that the binding energy of a species, B , to an already existing cluster (or complex) of species, $\{A_1, \dots, A_n\}$, which we collectively call C , is given by the simple formula,

$$E_b(B, C) = E_b(B, A_1, \dots, A_n) - E_b(A_1, \dots, A_n). \quad (4)$$

This result will be particularly useful when we consider the additional binding of a vacancy or solute to an already existing vacancy-solute complex.

We have quantified a number of uncertainties in the formation and binding energies presented in this work. Test calculations were performed to determine the combined convergence error from our choice of k-point sampling and plane-wave cutoff energy. For interstitial C and N solutes in a defect-free lattice, formation energies were converged to less than 0.05 eV and formation energy differences, such as migration energies, to less than 0.03 eV. For interstitial He the convergence errors were half of those for C and N. For configurations containing vacancies or self-interstitial defects, formation energies were converged to 0.03 or 0.07 eV, respectively, while binding energies were converged to 0.01 eV, except for the binding of He to a vacancy, where the error was 0.03 eV.

The zero-point energy (ZPE) contributions to the formation energy, which can be significant for light solute atoms, have not been calculated in this work. We performed calculations of the ZPE for He, C and N solutes in a number of test sites in afmD and afmI Fe, keeping the much heavier Fe atoms fixed, which is equivalent to assuming they have infinite mass³³. The results showed that the ZPE contributions were consistently around 0.10 eV in all cases, which we take as an estimate of the ZPE error on the formation energies of configurations containing C, N and He. The variation with site was, however, surprisingly low at 0.01 eV, which we take as an estimate

of the ZPE error in formation energy differences, binding energies and in the solution enthalpy for C, given that ZPE contribution in graphite is very similar to in Fe³³.

Performing calculations in a fixed supercell of volume, V , results in a residual pressure, P , for which an Eshelby-type elastic correction to the total and, therefore, formation energy^{57,58} of $E^{\text{corr.}} = -P^2V/2B$, can be applied. As such, $E^{\text{corr.}}$ also serves to indicate the likely finite-volume error. For many of the configurations considered here these corrections are negligible compared to other sources of error. Where they are significant, however, their relevance is discussed at the appropriate points in the text.

III. SOLUTES IN THE DEFECT FREE LATTICE

A. Single solutes

The formation energies for substitutionally and interstitially sited He, C and N solutes in the sites shown in Fig. 1 are given in Table I for Fe and Table II for Ni. We found that the Eshelby corrections were negligible for substitutional He but could be as high as 0.02 eV in magnitude for interstitial He and 0.04 eV for interstitial C and N. The corresponding uncertainties in formation energy differences were around half of these values. We discuss the results for He first, followed by those for C and N.

1. He solute

We found that He exhibits a large, positive formation energy in all sites but is most stable substitutionally, which is consistent with existing DFT studies of He in other bcc and fcc metals^{4,19,21–30}. The standard explanation is that, as a closed shell noble gas element, bonding interactions should be primarily repulsive, leading to insolubility and a preference for sites with the largest free volume^{21,26}. This result distinguishes He from other small solutes, such as C and N, which are more stable interstitially but also distinguishes it from substitutional alloying elements, such as Ni and Cr with formation energy differences between substitutional and interstitial sites in Fe of 3.0 eV and above^{48,59}.

In Fe, the influence of substitutional He on the local magnetic moments of atoms in its first nearest neighbour (1nn) shell was found to be similar to those for a vacancy, being generally enhanced relative to the bulk moment and by up to $0.38 \mu_B$ here. This is similar to He in bcc Fe^{25,26}. Indeed, we found that if the He atom was removed from the relaxed substitutional configuration with no further relaxation, the local 1nn Fe moments changed by less than $0.03 \mu_B$. In contrast to the vacancy, however, where 1nn Fe were displaced inwards by 0.09 and 0.02 Å in afmD and afmI Fe, respectively⁴⁸, the respective displacements around a substitutional He were, on average,

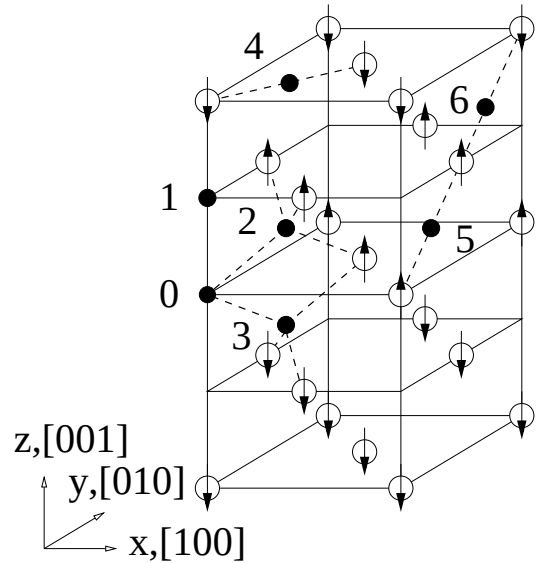


FIG. 1: Substitutional (0) and interstitial octahedral (1), tetrahedral (2-3) and crowdion (4-6) positions (in black) in afmD Fe. The Fe atoms are shown in white with arrows to indicate the local moments. Magnetic planes are included to aid visualisation. The afmD Fe state, which has the lowest symmetry, is shown to uniquely identify all distinct positions. In afmI Fe and Ni, positions 2 and 3 are equivalent by symmetry, as are 5 and 6. In Ni, position 4 is also equivalent to 5 and 6.

outwards by 0.02 and 0.04 Å. This contrast can also be seen in the formation volumes, which were found to be $0.74 V_{\text{bulk}}$ and $0.96 V_{\text{bulk}}$ for a vacancy, compared to $1.17 V_{\text{bulk}}$ and $1.38 V_{\text{bulk}}$ for substitutional He in afmD and afmI Fe, respectively. Results in Ni were very similar to Fe, with enhanced moments in the 1nn shell around both a vacancy and substitutional He, a contraction of 0.04 Å in the 1nn shell around a vacancy and an expansion of 0.02 Å around substitutional He. The formation volume for substitutional He, at $1.02 V_{\text{bulk}}$, was again found to be greater than that for the vacancy, at $0.66 V_{\text{bulk}}$.

The large formation energy difference, of around 2 eV, between substitutional He and the underlying vacancy in Fe and Ni [see Section IV], which must be due to chemical interactions, may seem at odds with the relatively inert behaviour of He mentioned above. However, similar results in bcc Fe have been reproduced using simple pair potentials^{60,61}, which demonstrates that such a large energy difference, once distributed over 1nn and 2nn bonds, is commensurate with the relatively small forces observed on the neighbouring Fe atoms around substitutional He.

In Fe, interstitial He was found to be most stable in the tetrahedral (tetra) site, the octahedral (octa) site being the next most stable and lying 0.206 and 0.059 eV higher in energy in the afmD and afmI states, respectively. There is no consistent ordering of the octa and tetra sites in ab initio studies of other fcc metals, with the octa site being most stable in Ag²¹, Al²³ and Pd^{21,24} and the tetra site being most stable in Cu²¹ and Ni^{19,21,22}, as

Config.	He		C		N	
	afmD Fe	afmI Fe	afmD Fe	afmI Fe	afmD Fe	afmI Fe
	E_f	E_f	E_f	E_f	E_f	E_f
	(ΔE_f)	(ΔE_f)	(ΔE_f)	(ΔE_f)	(ΔE_f)	(ΔE_f)
sub (0)	4.024 (—)	4.185 (—)	-6.981 (—)	-6.244 (—)	rlx (other)	-5.153 (—)
octa (1)	4.669 (0.206)	5.026 (0.059)	-8.797 (0.000)	-8.856 (0.000)	-8.602 (0.000)	-8.621 (0.000)
tetra uu (2)	4.529 (0.066)	as tetra ud	-6.535 (2.261)	as tetra ud	-6.917 (1.685)	as tetra ud
tetra ud (3)	4.464 (0.000)	4.967 (0.000)	-6.644 (2.153)	-6.272 (2.585)	-7.044 (1.558)	-6.737 (1.884)
[110] crow. (4)	rlx (3)	5.271 (0.303)	-6.764 (2.033)	-6.412 (2.445)	rlx (3)	-6.006 (2.614)
[011] crow. uu (5)	4.827 (0.364)	as [011] crow. ud	-7.354 (1.443)	as [011] crow. ud	-7.000 (1.602)	as [011] crow. ud
[011] crow. ud (6)	4.802 (0.338)	5.188 (0.221)	-7.487 (1.310)	-6.744 (2.113)	-7.218 (1.384)	-6.328 (2.293)

TABLE I: Formation energies, E_f , in eV, for substitutionally and interstitially sited solute atoms, as shown in Fig. 1. The formation energies in bold are for the most stable states. For He, which is most stable substitutionally, the most stable interstitial site is also highlighted. The formation energy differences, ΔE_f (in brackets), to the most stable interstitial configurations are also given, in eV. Where the configuration was found to be unstable the configuration to which it relaxed is given. The substitutional N configuration in the fct afmD state relaxed to one with an octa N at 1nn to a vacancy.

Config.	He	C	N
	E_f	E_f	E_f
	(ΔE_f)	(ΔE_f)	(ΔE_f)
sub (0)	3.185 (—)	-5.386 (—)	-4.562 (—)
octa (1)	4.589 (0.129)	-8.422 (0.000)	-7.520 (0.000)
tetra (2-3)	4.460 (0.000)	-6.764 (1.659)	-6.497 (1.023)
$\langle 110 \rangle$ crow. (4-6)	4.651 (0.191)	-6.795 (1.628)	-5.970 (1.550)

TABLE II: Formation energies, E_f , in eV, for substitutionally and interstitially sited He, C and N atoms in Ni. The layout and data content is as in Table I

our results for Ni confirm. In both Fe and Ni, however, He favours the tetra site, which gives a strong indication that the tetra site will also be the most stable interstitial site in concentrated Fe-Ni based austenitic alloys.

The other interstitial sites considered here lie no more than 0.364 eV above the tetra site, suggesting many low energy migration paths for interstitial He, that is, in the absence of any lattice defects that can act as strong traps.

The bilayer structure in afmD Fe breaks the symmetry of the octa site and a He atom placed there was found to spontaneously relax in the $[00\bar{1}]$ direction (as defined in Fig. 1), to between layers of the same spin by 0.55 Å. It is, perhaps, surprising that in both afmI Fe and Ni, an octa-sited He was also found to be unstable to small displacements in many directions. We present the results of these calculations in Table III.

It is particularly clear in the afmI Fe data that lower energy configurations were found along all of our test directions, with He relaxing to between 0.23 and 0.62 Å from the symmetrical position. The picture is less clear in afmD Fe, where He was generally found to relax to the lowest local energy minimum but other metastable positions were found. In Ni, the drop in energy is far less pronounced than in Fe but is still present, with He relaxing to stable positions 0.29 Å from the centre along $\langle 100 \rangle$ directions and 0.54 Å along $\langle 110 \rangle$ directions. These configurations are important, certainly as intermediate states for the migration of interstitial He, but also as potential transition states and already suggest a low migration energy barrier. We study these possibilities in detail in Section III B. For completeness, we also tested for the presence of stable off-centre positions for tetra-sited He but relaxation always returned He to the symmetrical position.

The displacements of 1nn Fe atoms around interstitially-sited He were, unsurprisingly, found to

Config.	afmD Fe		afmI Fe		Ni	
	E_f (ΔE_f)	Δr	E_f (ΔE_f)	Δr	E_f (ΔE_f)	Δr
octa sym.	rlx		5.208	0.00	4.617	0.00
	octa [00 $\bar{1}$]		(0.241)		(0.157)	
octa [100]	rlx		5.105	0.39	4.607	0.29
	octa [00 $\bar{1}$]		(0.138)		(0.147)	
octa [001]	4.812 (0.348)	0.30	5.026 (0.059)	0.50	as octa [100]	
	4.669 (0.206)	0.58	as octa [001]		as octa [100]	
octa [110]	rlx		5.079	0.54	4.589	0.54
	octa [00 $\bar{1}$]		(0.112)		(0.129)	
octa [011]	4.799 (0.335)	0.58	5.035 (0.068)	0.23	as octa [110]	
	rlx		as		as	
octa [01 $\bar{1}$]	octa [00 $\bar{1}$]		octa [011]		octa [110]	
	rlx		5.029	0.62	rlx	
octa [111]	tetra ud		(0.062)		tetra	
	rlx		as		as	
octa [11 $\bar{1}$]	octa [00 $\bar{1}$]		octa [111]		octa [111]	

TABLE III: Formation energies, E_f , and formation energy differences, ΔE_f , in eV, to the most stable tetra site (in brackets) for octa-sited He atoms in Fe. He is either sited symmetrically (sym.) or has been displaced off-centre, in which case the direction of the displacement is used to label the configuration and the displacement length after relaxation, Δr is given, in Å. The symmetrical position is as shown in Fig. 1 and directions determined from that point with the coordinate system shown. When no stable local energy minimum was found the state to which the configuration relaxed is given.

be greater than for the substitutional site. A tetra-sited He in afmI Fe displaced its neighbours by 0.23 Å. In afmD Fe, displacements of 0.22 and 0.32 Å were found for tetra uu and tetra ud -sited He, respectively. The magnetic moments on the 1nn Fe atoms were quenched relative to the bulk moments by 0.24 μ_B in afmI Fe and by 0.16 μ_B for the tetra uu site in afmD Fe but enhanced by 0.15 μ_B for the tetra ud site. We attribute this difference to the greater free volume into which 1nn Fe atoms around a tetra ud site may be displaced. We found formation volumes of 0.82 V_{bulk} and 0.99 V_{bulk} for tetra-sited He in afmI Fe and tetra-ud-sited He in afmD Fe, respectively. Once again, results in Ni were similar to Fe, with a 0.24 Å displacement and moment quench of 0.09 μ_B in 1nn Ni atoms around a tetra-sited He and a formation volume of 0.78 V_{bulk} .

In the most stable octa configuration in Fe, the local geometry is complicated by the displacement of He from the symmetrical position. For that reason, we define a

local unit cell surrounding the octa site using the positions of its six 1nn metal atoms, which lie at the centres of the cell faces, and report on the lattice parameters of that cell. In both afmI and afmD Fe, the local lattice parameter along [100] and [010] directions, a_{1nn} , is increased by 0.31 Å relative to the bulk equilibrium lattice, with the local lattice parameter along the [001] direction, c_{1nn} , exhibiting an increase of 0.26 Å in the afmD state and 0.29 Å in the afmI state. The local moment on the 1nn Fe atom that He is displaced towards is significantly quenched by 1.04 and 0.41 μ_B in the afmD and afmI states, respectively. In contrast, the other 1nn moments are moderately enhanced by between 0.03 and 0.17 μ_B . In Ni, the most stable off-centre octa position is along $\langle 110 \rangle$ directions from the symmetrical position. The resulting local unit cell, which exhibits a very slight shear, has $c_{1nn} \neq a_{1nn}$, with a_{1nn} increased by 0.31 Å relative to bulk and c_{1nn} by 0.28 Å. Local 1nn Ni moments were found to be quenched by between 0.02 and 0.08 μ_B .

These findings suggest that the relative stability of tetra over octa He, which is opposite to the order suggested by free volume arguments^{21,26}, may be best ascribed to the relative ease with which a tetra He may lower its purely repulsive interactions with neighbouring atoms by local dilatation. To further investigate this hypothesis in Fe we split the formation energy for unrelaxed and relaxed substitutional, octa and tetra He configurations into three terms, in a similar manner to the work of Fu *et al.*³⁷. The first is the formation energy, $E_f^{\text{def.}}$, of any underlying, atomically relaxed, defects, e.g. a single vacancy for substitutional He. The second is the mechanical energy, $E_f^{\text{mech.}}$, required to deform the Fe matrix containing those relaxed defects to the exact positions found in the configuration under study. The third is the energy change from chemical interactions, $E_f^{\text{chem.}}$, upon insertion of the solute into its final position with no further relaxation. We also define the insertion energy, $E_f^{\text{ins.}}$, as the sum of $E_f^{\text{mech.}}$ and $E_f^{\text{chem.}}$ i.e. the formation energy for insertion of a solute into any position in a relaxed Fe matrix containing any relevant defects. We take the insertion energy as a more appropriate measure of site preference than the (total) formation energy, E_f . The results are given in Table IV.

The substitutional site is clearly the most favoured, even in the unrelaxed state and by at least 2.25 eV once relaxed. In the unrelaxed lattice, an octa He is significantly more stable than a tetra He, as expected from purely repulsive interactions given the relative proximity of 1nn Fe in the two sites. Under relaxation the chemical bonding energy is significantly reduced and to a far greater degree in the tetra site. The positive mechanical deformation energy is also greater for tetra He but the net result is still to stabilise tetra over octa He. These results clearly show that the relative stability of He in tetra and octa sites can be understood as resulting from a balance between the energy required for local dilatation of the Fe matrix coupled with a purely repulsive Fe-He interaction, which we suggest could be easily modelled

Config.	$E_f^{\text{mech.}}$	$E_f^{\text{chem.}}$	$E_f^{\text{ins.}}$
afmD Fe + He			
sub, unrelaxed	0.136	2.150	2.286
sub, relaxed	0.167	2.045	2.212
tetra, unrelaxed	0.000	6.778	6.778
tetra, relaxed	1.330	3.134	4.464
octa, unrelaxed	0.000	5.804	5.804
octa, relaxed	0.755	3.914	4.669
afmI Fe + He			
sub, unrelaxed	0.023	2.662	2.685
sub, relaxed	0.155	2.073	2.228
tetra, unrelaxed	0.000	6.774	6.774
tetra, relaxed	0.999	3.968	4.967
octa, unrelaxed	0.000	6.081	6.081
octa, relaxed	0.855	4.171	5.026

TABLE IV: Mechanical deformation energy, $E_f^{\text{mech.}}$, and chemical bonding energy, $E_f^{\text{chem.}}$, contributions to the total formation energy, E_f , and the insertion energy, $E_f^{\text{ins.}}$, for unrelaxed and relaxed substitutional, tetra and octa He solute configurations in afmD and afmI Fe, in eV. The most stable octa configuration was used in both states and the tetra ud configuration was used for the afmD state.

using a simple pair potential.

In bcc Fe, the relative stability of tetra over octa He has been explained as resulting from strong hybridisation of He p-states with Fe d-states^{21,26}. However, we do not find the evidence for such strong hybridisation to be convincing. We suggest that a repulsive non-bonding mechanism also applies to bcc Fe and explains the difference in a much simpler manner. The magnetic and polarisation effects discussed by Seletskiaia²⁶ and Zu²¹ are a simple consequence of these non-bonding interactions and not He p-state, Fe d-state hybridisation. Formation energy calculations^{21,26} show that octa-sited He is higher in energy both before and after relaxation, despite the relaxation energy for octa He being greater than for tetra He. This results, primarily, from the very short 1nn Fe-He separations in the octa site when compared to those for the tetra site and the relative strengths of the resulting repulsive interactions. The fact that purely repulsive pair potentials for Fe-He interactions in bcc Fe are capable of reproducing the relative stability^{60,61} gives further support to our claim.

2. C and N solutes

The results for C and N solutes [in Tables I and II] show that both elements clearly favour the octa interstitial site in both Fe and Ni. Experimental observations show this to be the preferred site for C in an Fe-13wt%Ni-1wt%C austenitic alloy⁶². One exception worth comment is that of substitutional C in afmD Fe, for which the insertion

energy, $E_f^{\text{ins.}}$, which as discussed for He provides a more appropriate measure of site preference, is comparable to that for octa C. On further inspection we found that, due to the asymmetries in the afmD state, the initially on-lattice C atom relaxed to 0.77 Å from the lattice site. While this displacement is certainly significant, the C atom remains closer to the substitutional site than to an octa position at 1nn to the (vacated) lattice site and has been named to reflect this difference. Relaxation of the substitutional N configuration also resulted in displacement away from the lattice site but convergence was to a configuration with the N atom in an octa site at 1nn to a vacancy. We performed calculations to test for the presence of any stable off-centre octa configurations for C and N but none were found, in contrast to the results for He.

We discuss the influence of octa C and N solutes on the local lattice geometry in an identical manner to octa-sited He, that is, using $a_{1\text{nn}}$ and $c_{1\text{nn}}$. The results are presented in Table V for both Fe and Ni, including results in fm-HS Fe, which was shown to be mechanically unstable in our previous work⁴⁸, but not to the isotropic strain exerted locally by an octa-sited solute. We include this extra state here to compare with the work of Jiang and Carter³³. It is immediately clear that the geometrical influence of octa C is rather similar to octa N, although with slightly smaller dilatations for N. Local expansion is observed in all our reference states, although the expansion of c in afmD and afmI Fe is much less than for a . As a result, the local c/a ratio is significantly reduced relative to the bulk material, to 1.02 around a C solute in both afmD and afmI Fe, which is in good agreement with the 3% tetragonal distortion found by Boukhvalov *et al.*⁴², and to 1.01 and 1.02 around an N solute in afmD and afmI Fe, respectively.

The magnetic influence of octa C and N solutes is, again, very similar with significant quenching of the local moments on 1nn solvent atoms seen in all reference states, as expected for magnetic atoms under compression. In both afmD and afmI Fe the effect is most pronounced in those neighbours lying within the same magnetic plane as the solute, which also show the most significant displacement, resulting in a quench of 0.72(0.66) μ_B for C(N) in afmD Fe and of 1.25(1.37) μ_B in afmI Fe. In fm-HS Fe, 1nn moments are quenched by 0.48(0.57) μ_B around C(N) and in Ni a quench of 0.42 μ_B was observed for both C and N.

In addition to this local influence, we have investigated the dependence of the lattice parameters of our reference states on the fractional atomic compositions, x_C^f and x_N^f for C and N, respectively. For low concentrations, as studied here, the lattice parameters change linearly as a function of the fractional composition⁶³. In this case, quantities such as $\Delta a/(ax_C^f)$, where Δa is the difference between the lattice parameter with and without solute atoms present, are dimensionless constants that completely specify the linear expansion. Our calculations have been performed in supercells at the equilibrium lat-

	afmD Fe		afmI Fe		fm-HS Fe		Ni	
	C	N	C	N	C	N	C	N
Δa_{1nn}	0.321	0.303	0.305	0.276	0.174	0.145	0.183	0.170
Δc_{1nn}	0.080	0.048	0.154	0.127				
c_{1nn}/a_{1nn}	1.016	1.013	1.023	1.023				
$\Delta a/(ax_X^f)$	0.266	0.265	0.341	0.327	0.072	0.034	0.243	0.263
$\Delta c/(cx_X^f)$	-0.057	-0.044	0.026	0.042				
$\Delta a_{\text{eff.}}/(a_{\text{eff.}}x_X^f)$	0.158	0.162	0.236	0.232				
V_f/V_{bulk}	0.53	0.54	0.78	0.76	0.214	0.102	0.73	0.79
$E_{f,G}^{\text{sol.}}$	0.323		0.263		-0.164		0.697	

TABLE V: Lattice parameter differences (Δa_{1nn} and Δc_{1nn} , in Å) between those for the unit cell surrounding octa C and N solutes (a_{1nn} and c_{1nn}) and the bulk equilibrium lattice parameters and the local c_{1nn}/a_{1nn} ratio. Linear expansion coefficients ($\Delta a/(ax_X^f)$ and $\Delta c/(cx_X^f)$) for the dependence of the lattice parameters on the fractional atomic solute composition, x_X^f , for solute X. For afmD and afmI Fe, the linear expansion coefficient for an effective lattice parameter, defined by $a_{\text{eff.}} = (a^2c)^{1/3}$ is also given. Fractional formation volumes, V_f/V_{bulk} for octa-sited C and N solutes are given. The solution energy, $E_{f,G}^{\text{sol.}}$, taken to dissolve graphite in each of the reference states is given, in eV. For comparison, our calculations in bcc fm Fe give $E_{f,G}^{\text{sol.}} = 0.700$ eV.

tice parameters, so we determine the linear expansion coefficients by extrapolating to zero stress using the residual stress that builds up on the supercell upon addition of a solute and a knowledge of the elastic constants [see Section II]. In afmD and afmI Fe we have also calculated the linear expansion coefficients for an effective lattice parameter, $a_{\text{eff.}} = (a^2c)^{1/3}$, as a means to compare more directly with experiment.

The results [in Table V] show that local expansion around the solutes leads to a net expansion of the cell, overall. The afmD state of Fe does, however, exhibit a small contraction in c and the afmI state shows very little expansion in c , when compared to that for a . Once again, this shows that the addition of C and N acts to reduce the c/a ratio, bringing the lattice back toward perfect fcc. In austenite, experimental results by Cheng *et al.*⁶³ and presented by Gavriljuk *et al.*⁴⁰ show that $\Delta a/(ax_C^f)$ lies between 0.199 and 0.210, with $\Delta a/(ax_N^f)$ being slightly greater at between 0.218 and 0.224. Our results in afmD and afmI Fe are in broad agreement with these values but do not differentiate between C and N. Results in fm-HS Fe are significantly different from experiment, which again shows the unsuitability of this state for modelling austenite. It is interesting to note that our results for Ni are consistent with those for austenite and do exhibit more expansion due to N than for C. Experimental results in austenitic FeCrNi alloys⁴⁰ are comparable to those for pure austenite and the general agreement with our results strengthens the case for using afmD and afmI Fe or using Ni as model systems for austenite and austenitic alloys.

We have determined the solution energy at fixed equilibrium volume, $E_{f,G}^{\text{sol.}}$, taken to dissolve graphite into our four bulk states [Table V]. We have done this by calculating the solution energy relative to diamond and then applying the commonly accepted experimental energy difference of 20 meV/atom between the cohesive energies of

diamond and graphite at $T = 0$ K⁶⁴. For comparison, we have calculated $E_{f,G}^{\text{sol.}}$ for C in bcc fm Fe and find a value of 0.70 eV, which is in good agreement with the experimental value of between 0.60 and 0.78 eV found by Shumilov *et al.*^{33,65}.

The solution energies in all three Fe states are significantly lower than for bcc fm Fe. This is consistent with the relatively higher solubility of C in austenite than in ferrite and with the well known experimental result that C stabilises austenite over ferrite, as seen in the phase diagram. The effect is most pronounced in the fm-HS state, where the reaction is exothermic, in good agreement with previous DFT calculations³³. In combination with the results discussed above, this implies that at sufficient concentrations, C will act to stabilise the fm-HS state over the others, just as was found for Ni in fcc Fe-Ni alloys⁶⁶. The same conclusions follow for N by a direct comparison of the formation energies for octa sited N [see Table I], for which we found values of -8.252 and -9.018 eV in bcc fm and fcc fm-HS Fe, respectively.

Experimental results for the solution enthalpy of C in austenite⁶⁷ yield a value of $E_{f,G}^{\text{sol.}} = 0.37$ eV at the concentration studied here, which agrees to within 0.1 eV with our calculations in afmD and afmI Fe but not with those for the fm-HS state and again supports their suitability as reference states for paramagnetic austenite. Our calculations in the ferromagnetic state for Ni are in good agreement with previous DFT calculations of Siegel and Hamilton⁶⁸. However, as they report, this value is higher than those found experimentally in high-temperature, paramagnetic Ni, which lie between 0.42 and 0.49 eV. It is worth noting that their calculations in non-magnetic (nm) Ni, which they use to model the paramagnetic state, underestimate the experimental range at between 0.2 and 0.35 eV. We conclude that the calculated solution enthalpy for C in Ni is particularly sensitive to the underlying magnetic state.

B. Solute migration

As a first step in the calculation of migration energies for He, C and N solutes we investigated whether a 32 atom cell would be sufficient for this purpose. To do this we recalculated the formation energies for substitutional and interstitial He and C in afmD Fe using a 32 atom cell. We compare these with our 256 atom cell calculations [Table I] in Table VI.

Config.	He		C	
	32 atom	Error	32 atom	Error
	E_f	E_f	E_f	E_f
	(ΔE_f)	(ΔE_f)	(ΔE_f)	(ΔE_f)
Sub (0)	4.039	0.015	-6.911	0.070
	(—)	(—)	(—)	(—)
octa (1)	4.730	0.061	-8.798	-0.001
	(0.151)	(-0.055)	(0.000)	(0.000)
tetra uu (2)	4.607	0.078	-6.395	0.140
	(0.028)	(-0.038)	(2.403)	(0.142)
tetra ud (3)	4.579	0.115	-6.544	0.100
	(0.000)	(0.000)	(2.255)	(0.102)
[110] crow. (4)	rlx (3)	rlx (3)	-6.396	0.368
			(2.402)	(0.369)
[011] crow. uu (5)	4.897	0.070	-7.209	0.145
	(0.318)	(-0.046)	(1.589)	(0.146)
[011] crow. ud (6)	4.866	0.064	-7.346	0.141
	(0.287)	(-0.051)	(1.452)	(0.142)

TABLE VI: Comparison between calculations in 32 atom and 256 atom cells in afmD Fe of the formation energies, E_f , in eV, for substitutional and interstitial He and C solutes and formation energy differences, ΔE_f , in eV, to the most stable interstitial configurations, highlighted in bold. The layout and data content of each column is as in Table I. The column headed, 32 atom, contains the results for the 32 atom cell and the column headed, Error, contains the difference between the 32 atom and 256 atom results, which we take as an estimate of the finite volume error in the 32 atom cell.

There is a significant size effect on the formation energies in the 32 atom cell, except for substitutional He and octa C, where the formation energies are within errors of those in the 256 atom cell. The formation energies are greater in the 32 atom cell, as expected from volume-elastic effects, by between 0.06 and 0.12 eV for interstitial He and by between 0.00 and 0.37 eV for interstitial C. Formation energy differences to the most stable interstitial configuration also exhibit a significant size effect, with the smaller cell underestimating them by between 0.04 and 0.06 eV for He configurations and overestimating them by between 0.10 and 0.37 eV for C. It is reasonable to assume that the migration energy, which is itself a formation energy difference, will suffer from similar size

effects.

For C, the choice of cell size actually changes the relative stability of the [110] crowdion and tetra ud configurations. This is important as these two are transition states on two distinct migration paths for C (as will be shown in what follows). The small cell would, therefore, give the wrong minimum energy path (MEP), as found previously for C in fm-HS Fe³³. Closer inspection of the [110] crowdion configuration showed that the periodic boundary conditions in the smaller cell applied unphysical constraints on the displacements of Fe atoms at 1nn to C and along the crowdion axis generally, which resulted in a significant buckling, moving the C atom towards the tetra uu site, that is along [001], by 0.71 Å. In the larger cell these constraints are not present, resulting in a significantly lower formation energy and while there is still a small displacement towards the tetra uu site of 0.18 Å this is to be expected given the asymmetry present in the afmD state.

As a final test, we investigated the case of C in fm-HS Fe, where Jiang and Carter have determined a migration barrier in a 32 atom cell³³. They found that the $\langle 110 \rangle$ crowdion site is an intermediate site for C migration, lying only 0.01 eV below the transition state energy and 0.98 eV above the stable octa site. Our calculations in a 32 atom cell agree well with this finding, with an energy difference of 1.01 eV between the $\langle 110 \rangle$ crowdion and octa sites for C. However, when we repeated the calculations in a 256 atom cell, we found that a configuration with C in the $\langle 110 \rangle$ crowdion was structurally unstable and spontaneously transformed as a result of the non-isotropic stress on the Fe lattice. By contrast, the isotropic stress from an octa-sited C only led to local relaxation of the Fe matrix and maintenance of the crystal structure. We conclude that the 32 atom cell effectively imposed artificial constraints that allowed a, seemingly, sensible migration barrier to be determined.

Overall, we find that the finite size effects in the 32 atom cell are too significant and while some intermediate cell size between the two investigated here may be sufficient, we have performed our migration energy calculations in the 256 atom cell.

1. Interstitial He migration

The migration of interstitial He is relevant in the initial stages after He production by transmutation, α -particle irradiation and at sufficiently high temperatures for He to escape from defect traps. The migration of He between adjacent tetra sites (that is, between sites at 1nn on the cubic sub-lattice of tetra sites) can proceed along many distinct paths, with their corresponding transition states defining the energy barrier for the transition. A direct path would lead to an intermediate state with He in the crowdion position but the energy differences to the tetra configurations (in Tables I and III) suggest that the direct path is not the MEP and that the transition state has He

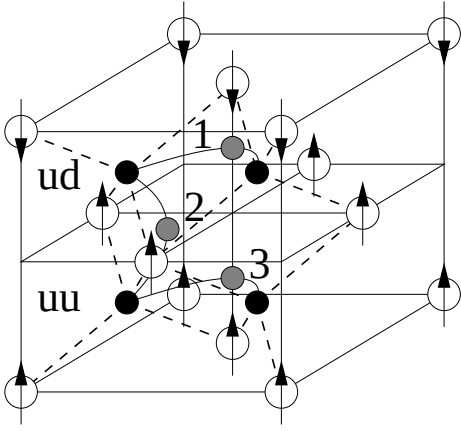


FIG. 2: Possible migration paths for interstitial He in the afmD Fe lattice. Paths are shown for 1nn jumps from initial to final tetra positions (black circles) via off-centre octa intermediate transition state positions (grey circles). The Fe atoms (white circles) are shown with arrows to indicate the local moments. The symmetry of the afmD state leads to two distinct tetra sites (uu and ud) and three distinct 1nn jumps, as shown. In the afmI state paths 1 and 3 are equivalent but still distinct from path 2. Coordinate axes are as in Fig. 1.

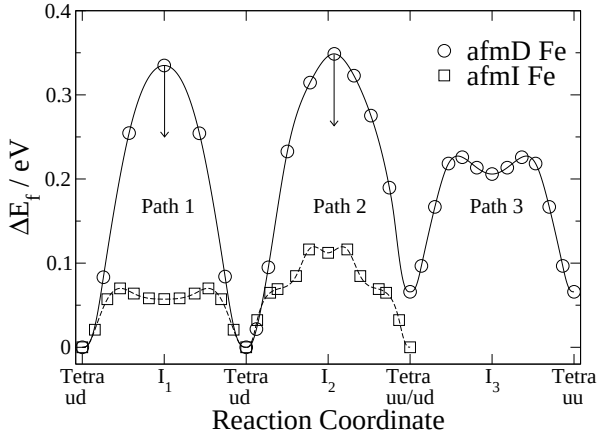


FIG. 3: Formation energy difference, ΔE_f , to the lowest energy tetra configuration along the distinct migration paths for interstitial He in Fe, as shown in Fig. 2. Positions of the tetra configurations and the intermediate configurations, I_i , along path i are labelled. In the afmI state, the data for path 3 has been omitted as it is equivalent to path 1. The arrows indicate the expected lowering of the migration barrier heights if a reorganisation of magnetic moments is allowed along the migration path.

in an off-centre position. We show representative paths for the three distinct 1nn jumps in afmD Fe in Fig. 2.

We have performed NEB calculations for He migration in Fe along these paths and show the formation energy difference to the most stable interstitial configuration against a, suitably chosen, reaction coordinate in

Path, i	afmD Fe	afmI Fe	Ni
1	0.335	0.070	0.129
2 (ud to uu)	0.349	0.119	—
2 (uu to ud)	0.283	—	—
3	0.160	—	—

TABLE VII: Migration energy barrier height, E_m , in eV, for the migration of interstitial He along the distinct paths identified in Fig. 2. In afmD Fe, path 2 is asymmetrical and the direction of migration has been identified by the initial and final tetra sites. In Ni, all paths are equivalent and the migration energy is given by the formation energy difference between the octa [110] and tetra He configurations from Tables II and III.

Fig. 3, with the corresponding migration barrier heights given in Table VII. It is immediately obvious that the results for the two Fe reference states differ significantly. This is not surprising, however, given that typical magnetic effects can be of the same order of magnitude as the migration barrier height [see Table III]. The high barriers along paths 1 and 2 in afmD Fe are because the lowest-energy tetra site is between layers of unlike moment and so not adjacent to the lowest energy octa intermediate site, which lies off-centre between like-spin layers [Table III]. A wholesale reorganisation of spins would lower the barriers along these paths and would be preferred in the paramagnetic state. This problem is not present for path 3, resulting in a significantly lower barrier, which is more consistent with those found in the afmI state, where a more uniform distribution of energies around the octa site exists [see Table III]. Path 1 in the afmI state and path 3 in the afmD state both show a double peaked structure with weakly stable octa [001] and octa [00 $\bar{1}$] intermediate states, respectively. These intermediates are equidistant from four tetra sites, resulting in the same energy barrier for 1nn and 2nn jumps on the tetra sublattice. The same cannot be said for migration along path 2, which proceeds via a (near-)octa [110] transition state in both reference states. In the afmI state, there appears to be a very shallow minimum at I_2 , that is the off-centre octa [110] configuration, but with a depth of 0.007 eV this may well be just an artefact of the convergence criteria as it is less than the expected error for formation energy differences. The data also exhibits a shoulder between the tetra ud and I_2 sites, which we suggest results from close proximity to the octa [111] configuration. It seems reasonable to suggest that the barriers for 2nn jumps that cross a magnetic plane will be close in energy to those for path 2, given the additional data in Table III. Overall, our findings suggest an energy barrier for interstitial He migration in austenite that is below 0.35 eV and more likely in the region between 0.1 and 0.2 eV.

Such low migration barriers are typical of all metals for which data is available. Ab initio calculations find a value of 0.10 eV for fcc Al²³, 0.07 eV for fcc Pd²⁴ and 0.06 eV for bcc Fe²⁵, W²⁷ and V³⁰. Experimental vali-

dation of these results is not forthcoming, primarily due to the low temperatures involved and the complications of He interactions within the material. In bcc W, Wagner and Seidman⁶⁹ estimate the migration enthalpy to be between 0.24 and 0.32 eV, with He being immobile up to temperatures of at least 90K, which is consistent with the value of 0.28 eV found for ³He migration by Amano and Seidman⁷⁰. The discrepancy between ab initio and experiment was explained by Becquart and Domain as being due to the presence of strong He-He binding, as found in their ab initio calculations, resulting in the formation of less mobile interstitial He clusters for all but the lowest concentrations²⁷. This is consistent with the work of Soltan *et al.*⁷¹, who found He to be mobile in W and Au at temperatures below 5K but with increasing suppression of mobility as a function of He concentration.

To this data we add the results of our own investigation into He migration in Ni. Following on from the results in afmD and afmI Fe, we make the reasonable assumption that the most stable off-centre octa He configuration is a good candidate for the transition state for interstitial He migration. The additional uncertainty on the inferred migration barrier height from this assumption should be less than 0.01 eV. From the results presented in Table III this is the off-centre octa $\langle 110 \rangle$ configuration, with a corresponding migration barrier height of 0.13 eV, which compares well with the experimental value of 0.14 ± 0.03 eV measured by Philipps and Sonnenberg⁷², corresponding to a migration activation temperature of 55 ± 10 K. This barrier height also compares well with our best estimate for austenitic Fe. We therefore tentatively suggest that the barrier height for interstitial He migration in austenitic Fe-Ni based alloys will be in the range 0.1 to 0.2 eV, resulting in free, three-dimensional diffusion well below room temperature. We accept that there is a very real possibility of significant local composition dependence in these concentrated alloys but we speculate that the effective barrier height will still be in the given range.

2. Substitutional He migration

The diffusion of substitutional He generally proceeds via the dissociative and vacancy mechanisms^{7,13,73}. Direct exchange with a neighbouring solute atom provides an alternative mechanism⁷³ but is highly unlikely to contribute significantly to diffusion due to the large activation energy for the process. For example, our best estimate of the barrier height in Ni is 3.50 eV, which compares well with that found using an embedded atom model (EAM) potential of 3.1 eV by Adams and Wolfer⁷³ and means that substitutional He is, essentially, immobile.

For many applications, substitutional He is best considered as an interstitial He atom strongly bound to a vacancy point defect, with a binding energy, $E_b(\text{He}^I, V)$.

The dissociative mechanism for substitutional He migration proceeds by the dissociation of He from a vacancy followed by interstitial migration until it becomes trapped in another vacancy. As such, the diffusion coefficient by this mechanism is inversely proportional to the vacancy concentration^{7,8,73}. If thermal vacancies dominate, the activation energy is given by^{7,8,13,73}

$$E_A^{\text{diss.}} = E_m(\text{He}^I) + E_b(\text{He}^I, V) - E_f(V), \quad (5)$$

where $E_m(\text{He}^I)$ is the migration energy for interstitial He. However, if there is a supersaturation of vacancies, for example under irradiation, then the diffusion is dominated by the dissociation step and

$$E_A^{\text{diss.}} = E_m(\text{He}^I) + E_b(\text{He}^I, V), \quad (6)$$

which is, essentially, the dissociation energy for substitutional He from its vacancy, and the diffusion coefficient will remain inversely proportional to the vacancy concentration^{8,73}.

The diffusion of a substitutional solute by the vacancy mechanism in an fcc lattice is usually well described by the 5-frequency model of Lidiard and LeClaire^{74,75}. A key assumption of this model is that when a vacancy binds at 1nn to a substitutional solute, the solute remains on-lattice. However, this is not the case for He, which we find relaxes to a position mid-way between the two lattice sites to form a $V_2\text{He}$ complex. The possibility of solute-vacancy exchange at 2nn is also not included in this model, a point we will return to in the following discussion.

Given the strong binding between a vacancy and substitutional He at 1nn, which we discuss in Section IV A, we assume that the migration of the $V_2\text{He}$ complex, as a single entity, dominates the diffusion by the vacancy mechanism^a, with a migration energy, $E_m(V_2\text{He})$. The diffusion coefficient will be proportional to the $V_2\text{He}$ concentration, which is in turn proportional to the vacancy concentration and depends on the binding energy between a substitutional He and a vacancy, $E_b(\text{He}^S, V)$. The resultant activation energy for substitutional He migration by the vacancy mechanism is given by⁷,

$$E_A^{\text{vac.}} = E_m(V_2\text{He}) - E_b(\text{He}^S, V) + E_f(V) \quad (7)$$

when thermal vacancies dominate and by

$$E_A^{\text{vac.}} = E_m(V_2\text{He}) - E_b(\text{He}^S, V) \quad (8)$$

when there is a supersaturation of vacancies²⁵.

We have determined the migration energies for the $V_2\text{He}$ complex using a combination of NEB and single configuration calculations. In afmD and afmI Fe, where

^a Other processes may contribute and a model, generalising the five-frequency model of Lidiard and LeClaire, is needed for this situation.

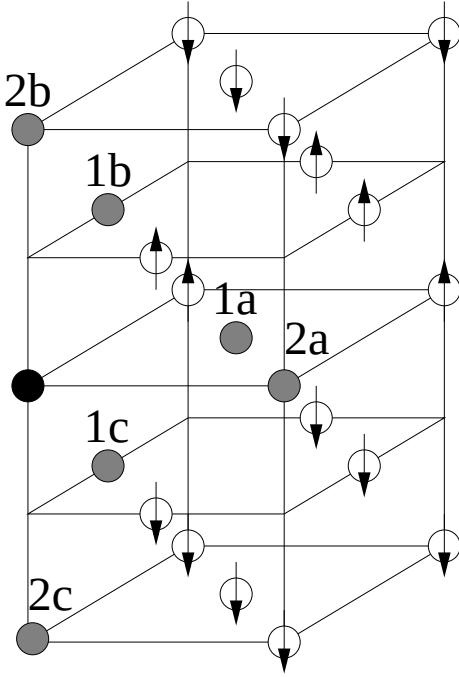


FIG. 4: Configurations for A-B pairs of interacting substitutionally sited solutes and defects in afmD Fe. Species A is shown in black and species B in grey along with the configuration label. Fe atoms are shown in white with arrows to indicate the local moments. Coordinate axes are as in Fig. 1.

more than one distinct $V_2\text{He}$ complex exists, we have calculated the migration energy along all of the distinct paths where the migrating Fe atom retains the sign of its magnetic moment. In previous work⁴⁸, we found unrealistically high migration barriers along paths where the moment changed. We label the migration paths for $V_2\text{He}$ migration by the initial and final configurations, which are defined in Fig. 4, and present the corresponding migration energies in Table VIII.

Path	afmD Fe	afmI Fe	Ni
1b→1b	1.033	as 1c→1c	1.197
1c→1c	0.910	0.898	—
1a→1b	1.216	—	—
1b→1a	1.211	—	—

TABLE VIII: Migration energies, $E_m(V_2\text{He})$, in eV, for the $V_2\text{He}$ complex. The migration paths are labelled by the initial and final configurations, as defined in Fig. 4.

The migration energies lie approximately 0.2 eV higher than those for the corresponding single vacancy migration in afmD and afmI Fe⁴⁸ and in Ni, where we found a vacancy migration energy of 1.06 eV, in good agreement with other DFT calculations^{22,47} and with the experimental average value⁷⁶ of 1.04 ± 0.04 . We suggest that this results from the additional energy required to

move the He atom from its central position in the $V_2\text{He}$ complex back towards the lattice site during migration, as observed in all cases. We also contrast these results with those for divacancy migration. In afmD Fe, afmI Fe and Ni we find migration energies for the divacancy along the 1b→1b path of 0.370, 0.221 and 0.473 eV, respectively, which are significantly lower than those for the $V_2\text{He}$ complex. In this case the difference arises not only from the energy required to move He to an on-lattice site during migration but also from its hindrance of the migrating Fe atom.

Vacancy-He exchange at 2nn provides an alternative migration path for substitutional He to that of $V_2\text{He}$ migration. We found energy barriers for 2nn exchange as low as 0.47 and 0.55 eV in afmD and afmI Fe, respectively, and a value of 0.94 eV in Ni. While these results are lower than the migration energies for $V_2\text{He}$, the repulsive interactions between a vacancy and substitutional He at 2nn [see Section IV A] mean that the equilibrium concentrations of such configurations will be significantly lower than the $V_2\text{He}$ concentration, resulting, we believe, in a much lower contribution to total diffusion. While this does strengthen our position that $V_2\text{He}$ migration dominates substitutional He diffusion by the vacancy mechanism, a model including all the relevant migration paths is necessary to answer this question conclusively.

Using the results presented here and in Section IV, we evaluate the expressions in Eqns. (5), (6), (7) and (8) and present the results in Table IX.

	afmD Fe	afmI Fe	Ni
$E_A^{\text{diss.}}$, Eq. (5)	0.599-0.788	0.853-0.902	1.405
$E_A^{\text{diss.}}$, Eq. (6)	2.411-2.600	2.810-2.859	2.756
$E_A^{\text{vac.}}$, Eq. (7)	2.066-2.413	2.232-2.251	2.192
$E_A^{\text{vac.}}$, Eq. (8)	0.254-0.601	0.275-0.294	0.841

TABLE IX: Activation energies for substitutional He migration, in eV, by the dissociative, $E_A^{\text{diss.}}$, and vacancy, $E_A^{\text{vac.}}$, mechanisms for thermal (Eqns. (5) and (7)) and supersaturated (Eqns. (6) and (8)) vacancy concentrations. For afmD and afmI Fe we give the range of possible values corresponding to the distinct migration paths in these states.

The results clearly differentiate between the two mechanisms and show a strong correlation to corresponding results in bcc Fe²⁵. When thermal vacancies dominate we predict that diffusion will proceed predominantly by the dissociative mechanism. If a supersaturation of vacancies exists then the vacancy mechanism clearly has the lowest activation energy. However, the vacancy concentration also plays a critical role in determining which mechanism dominates through the distinct way it enters the expressions for the diffusion coefficients. For sufficiently low but still supersaturated vacancy concentrations the dissociative mechanism may become dominant. This is, however, most likely to be the case at low tem-

peratures where diffusion by either mechanism is likely to be negligible. As such, we suggest that vacancy mediated diffusion is the most important mechanism in conditions of vacancy supersaturation.

For the case of Ni, Philipps and Sonnenberg⁶ find an activation energy for He diffusion of 0.81 ± 0.04 eV from isothermal, He-desorption spectrometry experiments. They attribute this result to the diffusion of substitutional He by the dissociative mechanism, hindered by thermal vacancies, from which they infer an energy for dissociation of He of 2.4 eV. Our results agree that substitutional He migration will proceed by the dissociative mechanism in a thermal vacancy population. There is, however, a 0.6 eV difference between our calculated activation energy [Table IX] and experiment. We also find a dissociation energy for He from the substitutional site of 2.756 eV, which is in excess of the inferred experimental value. This large discrepancy suggests that the inferred experimental mechanism may not be correct. Ab initio calculations show that interstitial He atoms bind strongly to one another in Ni²². As discussed earlier, just such a mechanism was responsible for the suppression of interstitial He migration in W and may also explain the experimental result in Ni.

3. Interstitial C and N migration

The migration of interstitial C and N in both Fe and Ni goes from octa site to adjacent octa site. In afmD Fe, there are three distinct migration paths, depending on where the initial and final octa sites lie. We label these as “in-plane”, when the octa sites lie in the same magnetic plane, “uu”, when the octa sites lie in adjacent magnetic planes with the same sign of magnetic moment and “ud”, when the octa sites lie in adjacent magnetic planes with the opposite sign of magnetic moment. In afmI Fe, only the “in plane” and “ud” paths are distinct and in Ni, all paths are equivalent. Each of these, distinct, migration paths will be symmetrical about an intermediate state lying in the plane that bisects the direct path between the two octa sites. In what follows, we consider the tetra and $\langle 110 \rangle$ crowdion sites as candidate intermediate states. Possible migration paths for in-plane migration in afmD Fe are shown in Fig. 5, as an example.

For C, the results in Tables I and II show that the crowdion configurations are the lowest lying of the possible intermediate states. We have performed NEB calculations in afmD Fe for C migrating from the octa site to all of the distinct crowdion sites in order to determine the energy profiles along these paths. We find a single maximum in the energy at the crowdion configurations. We find this is also the case for N migration via the crowdion configuration in Ni, as will be discussed below. On this basis and given the significant local dilatation necessary to form a crowdion, we make the assumption that there will be a single energy maximum at all $\langle 110 \rangle$ crow-

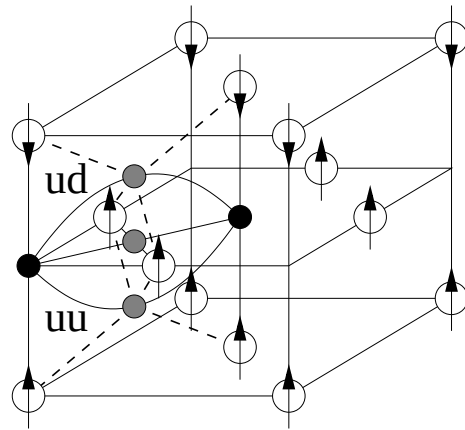


FIG. 5: Possible migration paths for interstitial C and N in afmD Fe. Paths are shown for migration from initial to final octa sites (black circles) lying in the same magnetic plane via tetra ud, $[110]$ crowdion and tetra uu intermediate sites (grey circles). Fe atoms (white circles) are shown with arrows to indicate the local moments. Migration between octa sites in adjacent magnetic planes have not been shown for clarity. Coordinate axes are as in Fig. 1.

dion sites so that the MEPs and barrier heights for C migration in afmD and afmI Fe and in Ni can be determined from the data in Tables I and II. The same can also be said for N migration in afmD Fe along uu and ud paths. For all other cases, however, the tetra sites are lower in energy and we have performed NEB calculations with climbing image⁷⁷ to investigate the migration energy profiles along these paths.

In afmD Fe, our calculations confirm that the tetra ud site is the energy barrier for N migration. In afmI Fe, however, there is evidence of a shallow minimum, 0.015 eV deep, around the tetra configuration. Results in Ni, by contrast, show a clear double-peaked structure in the energy profile. We present the results in Fig. 6 and include the results for migration via the crowdion site for comparison. The results show that the tetra N configuration is a stable local minimum, with a depth of 0.273 eV relative to the transition state, and not a saddle point, like the crowdion configuration. Despite this, the MEP for N migration is still via the tetra site.

We summarise our results for the energy barriers and MEPs for interstitial C and N migration in Table X. In the Fe reference states there is a significant spread in the migration barrier heights for C migration, both along distinct migration paths and between the two states. In-plane migration clearly exhibits a higher energy barrier in both states, which results directly from the tetragonal distortion of the lattice and the subsequently higher energy necessary to form the $[110]$ crowdion transition state. The data also suggests a significant dependence on the local magnetic order, just as was seen for interstitial He migration. The large spread in barrier heights means we cannot make any definitive predictions, except that diffusion is three-dimensional. However, in any thermo-

Path	C migration						N migration					
	afmD Fe		afmI Fe		Ni		afmD Fe		afmI Fe		Ni	
	E_m	TS/I	E_m	TS/I	E_m	TS/I	E_m	TS/I	E_m	TS/I	E_m	TS/I
in plane	2.033	[110] crow.	2.445	[110] crow.	1.628	$\langle 110 \rangle$ crow.	1.558	tetra ud	1.899	tetra*	1.296	tetra*
uu	1.443	[011] crow. uu		as ud		as in plane	1.602	[011] crow. uu		as ud		as in plane
ud	1.310	[011] crow. ud	2.113	[011] crow. ud		as in plane	1.384	[011] crow. ud	1.899	tetra*		as in plane

TABLE X: Migration energy barrier heights, E_m , in eV for interstitial C and N migration in afmD and afmI Fe and in Ni. Migration is between adjacent octa sites via a transition state/intermediate (TS/I), which is specified in the table, along all of the distinct paths for each particular reference state. Where the transition state/intermediate is only an intermediate state on the migration path, its name has been marked with an asterisk.

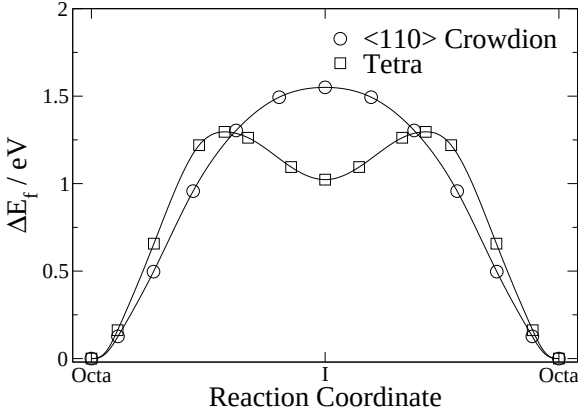


FIG. 6: Formation energy difference, ΔE_f , to the lowest energy octa configuration for N migration in Ni via tetra and $\langle 110 \rangle$ crowdion intermediate states.

dynamic average, the lower-energy paths will dominate, which suggests an effective barrier height around 1.4 eV in afmD Fe and 2.1 eV in afmI Fe. The afmD Fe value is reasonably consistent with the experimentally determined activation energies for C migration in austenite of 1.626 eV⁷⁸ and 1.531 eV⁷⁹.

In Ni, we find that C migrates via the crowdion site with an energy barrier height of 1.63 eV. This contrasts with the 32 atom cell, where the tetra pathway is preferred⁶⁸. Once again, this demonstrates the inadequacy of using a 32 atom cell for solute migration in fcc Fe and Ni. Experimental results, using a variety of techniques applied both above and below the Curie temperature, $T_C = 627$ K, for Ni, yield activation energies in the range 1.43 to 1.75 eV⁸⁰, consistent with our results. The experimental results also suggest that the influence of magnetism on the migration barrier (and enthalpy of solution) for C is no more than 0.2 eV and suggests this is the likely error in using fm Ni results to estimate those in the paramagnetic state.

Experimental results for C in Fe-Ni austenitic alloys, as discussed by Thibaux *et al.*⁸¹, show only slight changes in

C mobility as a function of Ni composition in the range from 20 to 100 wt% Ni. They also report an activation energy of 1.30 eV in an Fe-31wt%Ni austenitic alloy. Overall, our results, in conjunction with the experimental results we have discussed, suggest that the migration energy barrier for C migration will lie in the range 1.5 ± 0.2 eV across the whole composition range for Fe-Ni austenitic alloys.

For N, the migration barrier lies between 1.38 and 1.60 eV in afmD Fe, with a value of 1.90 eV in afmI Fe. As with C, the afmD Fe results are, on average, lower than those for the afmI state. The result of an Arrhenius fit to combined experimental diffusion data for N migration in austenite gave a similar value of 1.75 eV⁸⁰. In Ni, we find a barrier height of 1.30 eV, which is in excess of the experimental activation energy reported by Lappalainen and Anttila⁸² of 0.99 ± 0.12 eV. In light of the significant variation in experimental results for C migration in Ni, these two results are in reasonable agreement and certainly to within the 0.2 eV we have suggested earlier as a likely error when using ferromagnetic Ni to model the paramagnetic state. Overall, these results show that N migrates with a significantly lower barrier in Ni than in austenitic Fe and we would expect to find an intermediate value in Fe-Ni based alloys, more generally.

C. Solute-solute interactions

We have performed calculations to investigate the interactions between pairs of He atoms in substitutional and tetra sites in afmD and afmI Fe. Configurations with single substitutional and tetra-sited He atoms at up to 2nn separation were found to consistently relax to a vacancy containing two He atoms. While this does not yield any useful binding energy data it does indicate that there is little or no barrier for this process and places a lower limit on the capture radius of a substitutional He of around 3 Å. Results for pairs of interacting substitutional and tetra-sited He atoms, as identified in Figs. 4 and 7, respectively, are given in Table XI.

Substitutional He pairs show consistent results across the Fe reference states with a strong positive binding at 1nn and slightly repulsive interactions at 2nn [Table XI].

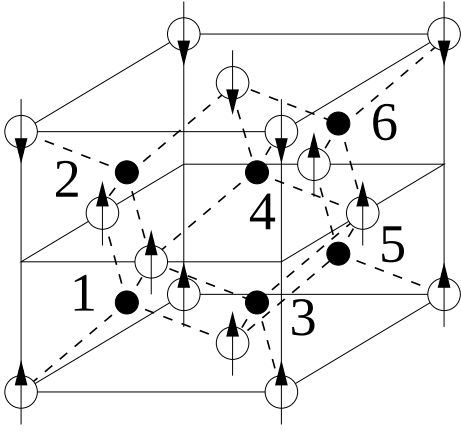


FIG. 7: Configurations for interacting tetra-sited solutes in afmD Fe. Configurations are labelled by the indices attached to the appropriate solute atom positions, shown in black. Fe atoms are shown in white with arrows to indicate the local moments. Coordinate axes are as in Fig. 1.

A-B/Config.	afmD Fe		afmI Fe	
	E_f	E_b	E_f	E_b
S-S/1a	7.115	0.934	7.423	0.946
S-S/1b	7.112	0.937	as S-S/1c	
S-S/1c	6.976	1.073	7.419	0.950
S-S/2a	8.197	-0.149	8.570	-0.201
S-S/2b	8.109	-0.060	8.493	-0.123
T-T/1-2	8.614	0.313	9.692	0.242
T-T/1-3	8.831	0.096	as T-T/2-4	
T-T/2-4	8.215	0.712	9.463	0.472
T-T/1-4	rlx T-T/2-5		9.403	0.531
T-T/1-5	8.700	0.227	as T-T/2-6	
T-T/2-6	8.643	0.284	9.428	0.506
T-T/2-5	8.487	0.440	9.340	0.594

TABLE XI: Formation and binding energies in eV for interacting pairs of He atoms in substitutional (S) and tetra (T) sites in afmD and afmI Fe. The configurations are labelled as in Figs. 4 and 7 for S-S and T-T pairs, respectively. In the afmD reference state the binding energies between tetra-sited pairs of He atoms have been calculated relative to two isolated tetra ud He. For interacting pairs of tetra-sited He atoms at 2nn and 3nn separation the configurations are labelled by the initial He positions, which due to the significant displacements under relaxation should not be taken as the final positions. Eshelby corrections for S-S pairs were found to be negligible but were -0.09 eV for T-T pairs with a resulting increase in the T-T binding energies of up to 0.05 eV.

In our calculations, He atoms at 1nn relax directly towards one another by between 0.38 and 0.44 Å, resulting in a consistent He-He separation of between 1.67 and 1.69 Å. While still close to the lattice sites, these displacements are in stark contrast to the insignificant displacements observed at 2nn. Substitutional He pairs in

Ni are similar: At 1nn the He atoms are displaced towards one another by 0.37 Å to a He-He separation of 1.75 Å. The resultant binding energy, at 0.657 eV, is less than in Fe but is in similar proportion to the substitutional He to vacancy binding energy [see Section IV A]. At 2nn He remains on-lattice with a repulsive binding energy of -0.16 eV.

Pairs of tetra-sited He atoms exhibit significant binding energies of up to 0.7 eV in afmD Fe and 0.6 eV in afmI Fe. Such strong interactions are consistently observed in bcc and fcc metals. Previous ab initio calculations found binding energies of 0.47 eV in Ni²², 0.7 eV in Pd²⁴ and Al²³, 0.4 eV in bcc Fe²⁵ and 1.0 eV in W²⁷. At 1nn separation, the He atoms in afmD and afmI Fe are displaced from the tetra sites only slightly under relaxation. The resulting He-He “bonds” all lie along one of the axes of the unit cell with lengths in a small range from 1.62 to 1.68 Å, which is consistent with those found for substitutional He pairs at 1nn. At 2nn and 3nn the He atoms displace significantly towards one another under relaxation from the initial tetra sites, resulting in He-He separations from 1.51 to 1.65 Å. These displacements are sufficiently large to take the He atoms either to the edge of their initial tetrahedral regions or into the adjacent octahedral region via one of the faces of the tetrahedron. This is most pronounced for the 3nn T-T/2-5 configuration, which in afmI Fe relaxed to a configuration with the He atoms within the octahedral region and symmetrically opposite the central position along the [111] axis. The situation is similar for the afmD state but one He atom is significantly closer to the central position. It is worth noting that this is the most stable configuration in afmI Fe and the second most stable in afmD Fe. The large binding energies result, simply, from the co-operative dilatation of the lattice and the reduction of repulsive He-Fe interactions, which are naturally greatest when the two He atoms are in close proximity. The results at 2nn and 3nn separations show that the local dilatation of the lattice around a single interstitial He results in an attractive force to other interstitial He atoms up to at least 3 Å away and encourages the formation of clusters.

To investigate interstitial cluster formation further we have determined the most stable configurations with three and four He atoms in afmD and afmI Fe. For a fixed number of He atoms we found many distinct configurations with similar energies but the most stable clusters were reasonably predictable from a simple pair interaction model, given the data in Table XI. In afmD Fe, the most stable He₃ configuration found had two He atoms in a 2-4 formation [see Fig. 7] with the third occupying the nearest octa site. In afmI Fe, the most stable was an L-shaped 1-2-3 cluster. In the most stable He₄ clusters, all He atoms occupied tetra sites in a rectangular-planar formation with 1nn edges, such as a 1-2-3-4 cluster. This is, in fact, the most stable arrangement found in afmI Fe, whereas in afmD Fe a square-planar configuration with all He atoms in tetra ud sites was the most stable. The

total binding energies for the most stable clusters are given in Table XII along with results in Ni²².

Cluster	afmD Fe	afmI Fe	Ni
He ₂	0.712	0.594	0.47
He ₃	1.537	1.374	1.25
He ₄	2.637	2.561	

TABLE XII: Total binding energies, in eV, for the most stable interstitial He clusters containing up to 4 He atoms. Results in Ni are from the work of Domain and Becquart²². Eshelby corrections were found to be -0.19 and -0.34 eV for He₃ and He₄ clusters, respectively, with corresponding increases in the binding energies of 0.14 and 0.27 eV.

The strong clustering tendency of interstitial He is clearly demonstrated by the data. Application of the Eshelby corrections only enhances this effect. The binding energy for an additional He, that is, $E_b(\text{He}_n) - E_b(\text{He}_{n-1})$, increases with n for the small clusters studied here. We would expect this, however, to plateau to an additional binding energy of around 1 eV per He atom in afmD and afmI Fe and in Ni, given that the co-operative dilatation of the lattice that gives rise to the binding happens locally. Such strong clustering can, not only, result in an effective reduction in interstitial He mobility as He concentration increases but is also a critical first step in the spontaneous formation of Frenkel-pair defects, as observed in gold⁸³. Indeed, the most stable He₄ configurations found here show a significant displacement of the nearest Fe atom to the cluster off-lattice by 0.94 Å in afmD Fe and 1.36 Å in afmI Fe. We consider this possibility further in Section IV B in the context of $V_m\text{He}_n$ clustering.

A-B/Config.	afmD Fe		afmI Fe	
	E_f	E_b	E_f	E_b
C-C/1a	-17.490	-0.104	-17.572	-0.141
C-C/1b	-17.487	-0.106	N/A	
C-C/1c	-17.559	-0.034	-17.561	-0.151
C-C/2a	-17.420	-0.174	-17.487	-0.226
C-C/2b	-17.617	0.023	-17.655	-0.058
N-N/1a	-17.010	-0.195	-17.037	-0.204
N-N/1b	-17.035	-0.170	N/A	
N-N/1c	-17.131	-0.074	-17.020	-0.221
N-N/2a	-17.054	-0.150	-17.075	-0.167
N-N/2b	-17.212	0.008	-17.172	-0.070

TABLE XIII: Formation and binding energies, in eV, for interacting pairs of octa-sited C and N interstitials. The configurations are as labelled in Fig. 8. Eshelby corrections were -0.03 and -0.06 eV in afmD and afmI Fe, respectively, with resultant increases in the binding energy of 0.02 and 0.03 eV.

Interactions between pairs of octa-sited C and N atoms

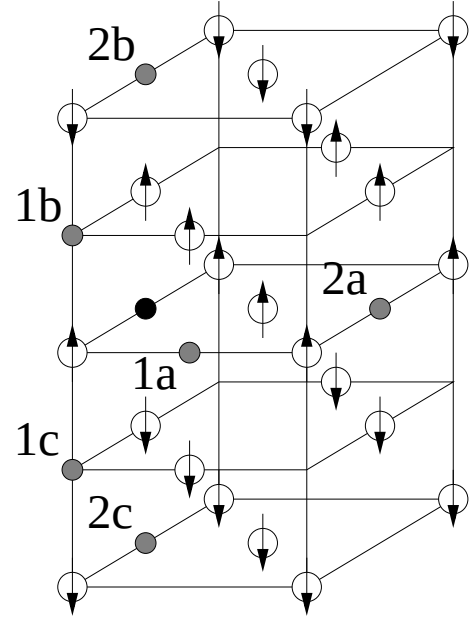


FIG. 8: Configurations for A-B pairs of interacting octa-sited interstitials in afmD Fe. Species A is shown in black and species B in grey along with the configuration labels. Fe atoms are shown in white with arrows to indicate the local moments. The lowest symmetry afmD state is shown to uniquely identify all of the distinct configurations. Some of these configurations will be symmetry equivalent in the afmI state. Coordinate axes are as in Fig. 1.

at up to 2nn separation in afmD and afmI Fe are given in Table XIII. The interactions are, generally, repulsive at both 1nn and 2nn, with a reasonable consistency between the two reference states, although the repulsion is slightly stronger in the afmI state. For C, the pair binding energy is between -0.1 and -0.15 eV at 1nn and more repulsive at 2nn at up to around -0.2 eV. By contrast, N pairs exhibit stronger repulsion than C at 1nn, at around -0.2 eV and weaker repulsion at 2nn, where the binding energy is at most around -0.15 eV. Calculations for C-C pairs at up to 4nn separation in afmI Fe found a maximal binding energy 0.02 eV. We conclude that there will be no appreciable positive binding of C-C and N-N pairs in our reference states for austenite.

Experimental determinations of C-C and N-N interaction energies in austenite are discussed in a review by Bhadeshia⁸⁴. If quasichemical theory, which only includes 1nn interactions, is used to interpret the existing thermodynamic data then a pair binding energy of -0.09 eV is found for C and -0.04 eV for N. Our results for C in afmD and afmI Fe are in good agreement with this value and while we do find a repulsive interaction between N-N pairs, we find a stronger repulsion than for C, which is contrary to the results of this analysis. A more detailed analysis can be performed using Mössbauer spectroscopy data to study the distribution of C atoms in the Fe matrix, which can be compared with the results of Monte Carlo simulations to determine the solute interaction en-

ergies at 1nn and 2nn⁸⁵. Such an analysis yields C-C binding energies of -0.04 eV at 1nn and less than -0.08 eV at 2nn and N-N binding energies of -0.08 eV and -0.01 eV at 1nn and 2nn, respectively⁸⁵. Our results follow the same pattern for the relative strengths of repulsion but are significantly in excess of the results of this analysis. The agreement is still impressive, however, given the level of extrapolation between our two ordered magnetic states at 0K and temperatures where paramagnetic austenite is stable.

For C in fm Ni, Siegel and Hamilton⁶⁸ found C-C binding energies at 1nn and 2nn of 0.01 and -0.01 eV, respectively, using comparative DFT calculations to those performed in this work. They, furthermore, show that this negligible level of binding is consistent with the experimental estimates of the C-C pair concentration as a function of total C concentration⁸⁶.

From the data presented above we would suggest that C-C and N-N interactions in Fe-based austenitic alloys will be repulsive at 1nn and 2nn, with binding energies in the range from -0.1 to -0.2 eV. We would, furthermore, expect the level of repulsion to be reduced as a function of increasing Ni concentration.

D. Interactions with substitutional Ni and Cr solutes in Fe

As an initial step in the investigation of the interactions of He, C and N with substitutional Ni and Cr solutes in austenite we have calculated the formation energies for single substitutional Ni and Cr and present the results in Table XIV.^b On this basis, the results of our calculations of the interactions between He, C and N solutes and substitutional Ni and Cr solutes in afmD and afmI Fe are presented in Table XV.

Config.	fct afmD		fct afmI	
	E_f	μ	E_f	μ
Sub. Ni	0.083	0.039	0.145	-0.301
Sub. Cr	0.263	0.843	0.061	1.120

TABLE XIV: Formation energies, E_f , in eV and magnetic moments, μ , in μ_B for substitutional Ni and Cr solutes in austenitic Fe. The sign of the moments indicates whether there is alignment (positive) or anti-alignment (negative) with the moments of the atoms in the same magnetic plane.

In both Fe reference states, substitutional He binds weakly to Ni, by around 0.1 eV, and has a repulsive interaction with Cr of -0.1 eV. The similarity to vacancy-substitutional Ni/Cr binding is striking⁴⁸. The similarity

^b These results agree to within errors with our previous work⁴⁸ at a lower plane-wave cutoff energy and direct the reader there for further discussion.

A-B/cfg	afmD Fe		afmI Fe	
	E_f	E_b	E_f	E_b
sub Ni-sub He/1a	4.032	0.076	4.212	0.117
sub Ni-sub He/1b	4.035	0.073	as 1c	
sub Ni-sub He/1c	4.018	0.090	4.233	0.097
sub Ni-tetra He/1b	4.496	0.051	4.979	0.133
sub Ni-tetra He/2a	4.500	0.047	5.078	0.034
sub Ni-tetra He/2d	4.480	0.067	5.062	0.050
sub Ni-octa C/1a	-8.692	-0.021	-8.717	0.006
sub Ni-octa C/1b	-8.673	-0.040	as 1c	
sub Ni-octa C/1c	-8.729	0.016	-8.643	-0.069
sub Ni-octa N/1a	-8.439	-0.080	-8.417	-0.058
sub Ni-octa N/1b	-8.432	-0.087	as 1c	
sub Ni-octa N/1c	-8.445	-0.074	-8.349	-0.126
sub Cr-sub He/1a	4.353	-0.065	4.284	-0.038
sub Cr-sub He/1b	4.358	-0.070	as 1c	
sub Cr-sub He/1c	4.433	-0.145	4.341	-0.095
sub Cr-tetra He/1b	4.609	0.118	4.883	0.145
sub Cr-tetra He/2a	4.746	-0.019	5.005	0.023
sub Cr-tetra He/2d	4.781	-0.054	5.024	0.004
sub Cr-octa C/1a	-8.647	0.114	-8.845	0.050
sub Cr-octa C/1b	-8.628	0.094	as 1c	
sub Cr-octa C/1c	-8.730	0.197	-8.826	0.030
sub Cr-octa N/1a	-8.597	0.258	-8.729	0.169
sub Cr-octa N/1b	-8.566	0.227	as 1c	
sub Cr-octa N/1c	-8.574	0.235	-8.704	0.145

TABLE XV: Formation and binding energies, in eV, for substitutional Ni/Cr (species A) to substitutional He, tetra He and octa C/N (species B) with configurations labelled as in Figs. 4, 9 and 10, respectively. Eshelby corrections to E_f were found to be -0.02 eV when interstitial solutes were present but negligible for all other quantities.

also extends to the local moments on 1nn atoms surrounding the substitutional He and vacancy, as was discussed in Section III. These results are also consistent with Ni and Cr acting as slightly oversized and undersized solutes, respectively, when interacting with point defects in afmD and afmI Fe, as discussed previously⁴⁸. We would expect the interactions of other transition metal solutes with substitutional He to be readily inferred from their interactions with vacancies.

Interstitial He binds weakly to Ni by, on average, 0.09 eV at 1nn and 0.05 eV at 2nn in the Fe reference states. We also observe weak positive binding with Cr, but only at 1nn, where the binding energy is, on average, 0.13 eV. Closer observations of the configurations revealed that He relaxed slightly away from Ni, but toward Cr at 1nn. Ni also remained closer to the lattice site than Cr. These geometrical results are consistent with Ni and Cr behaving as oversized and undersized solutes, respectively, despite both exhibiting binding to interstitial He, although the

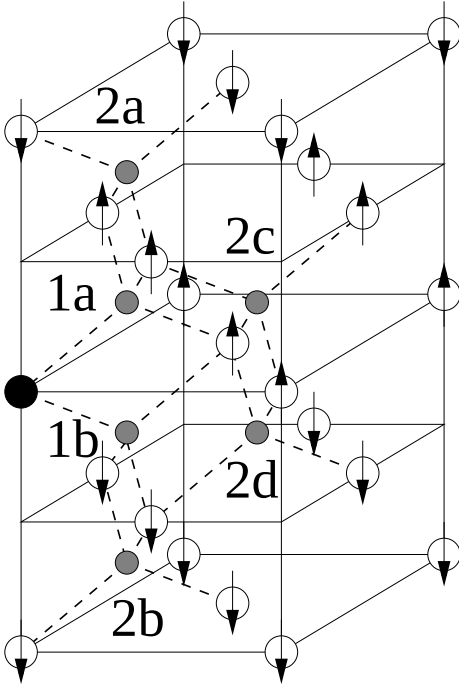


FIG. 9: Configurations for interactions between a substitutionally sited species (A) and a tetrahedrally sited species (B) in afmD Fe. Species A is shown in black, and species B in grey. Configurations are labelled by the position of the tetrahedrally sited species, as shown. Fe atoms are shown in white with arrows to indicate the local moments. Coordinate axes are as in Fig. 1.

binding to Cr is marginally greater. The level of binding suggests that Ni and Cr may act as weak traps for migrating interstitial He at low concentrations. However, with increasing concentration and, therefore, likelihood that He remains in similar local environments as it migrates, a direct study of the local composition dependence of the migration energy becomes necessary. From the binding energy data we can speculate, however, that such a dependence will also be weak and maintain our earlier suggestion that the activation energy for interstitial He migration will lie in the 0.1 to 0.2 eV range in concentrated Fe-Cr-Ni alloys.

The interactions of octa C and N with substitutional Ni and Cr are reasonably consistent in both afmD and afmI Fe. For C, interactions with Ni are minimal, although slightly repulsive, at 1nn, whereas positive binding is observed with Cr on the order of 0.1 eV. The interactions of N are similar to those of C but significantly stronger and exhibit a repulsion of around -0.1 eV to Ni and attraction to Cr of around 0.2 eV. The repulsive interactions with Ni are consistent with the lower solubility of C and, particularly, N in fcc Ni, compared to afmD and afmI Fe [see Tables I and II], and suggests that the interactions are cumulative. In the case of Cr, such cumulative interactions would encourage the formation of Cr-C/N complexes and the precipitation of Cr-carbonitrides, as observed exper-

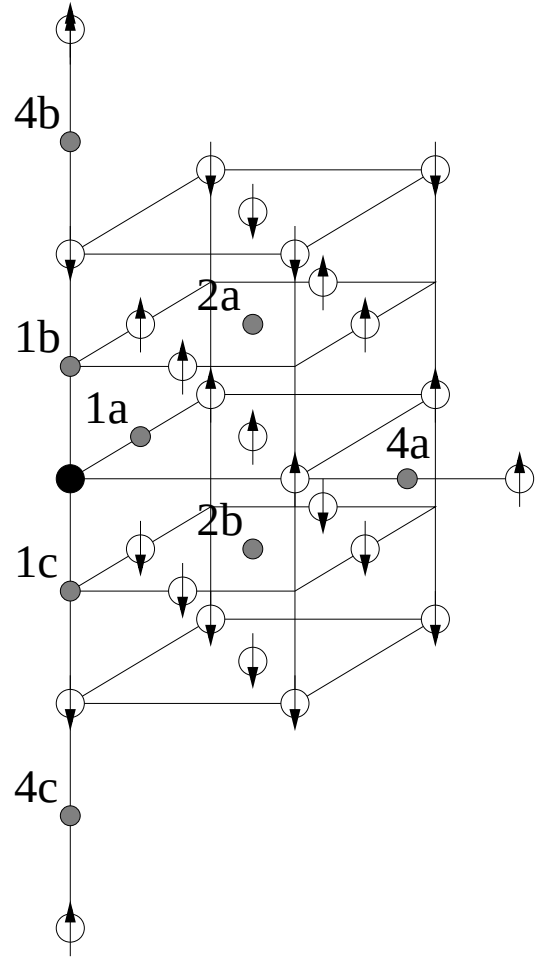


FIG. 10: Configurations for interactions between a substitutionally sited species A and octa-sited species B in the fcc/fct afmD reference state. Species A is shown in black and species B in grey along with the configuration labels. Fe atoms are shown in white with arrows to indicate the local moments. The lowest symmetry afmD state is shown to uniquely identify all of the distinct configurations. Some of these configurations will be symmetry equivalent in the afmI state. Coordinate axes are as in Fig. 1.

imentally in non-stabilised austenitic stainless steels⁸⁷, under conditions where these elements are mobile, that is at high temperatures or in irradiated environments.

IV. SOLUTE INTERACTIONS WITH POINT DEFECTS

In this section we consider the interactions of He, C and N with a single vacancy (V), in small vacancy-solute clusters, $V_m X_n$, and with the [001] self-interstitial (SI) dumbbell in afmD and afmI Fe and in Ni. We present the formation (and binding) energies of the underlying and most stable defects and defect clusters in Table XVI, as found previously⁴⁸. Pairs of vacancies were consistently most stable at 1nn separation. The most stable tetra-

vacancy cluster consists of a tetrahedral arrangement of vacancies at 1nn to each other. The most stable tri-vacancy cluster is formed from this by placing an atom near the tetra-vacancy centre. Finally, the most stable hexa-vacancy is an octahedral arrangement of vacancies with 1nn edges.

Defect	afmD Fe	afmI Fe	Ni
vacancy	1.812	1.957	1.352
di-vacancy	3.443 (0.181)	3.840 (0.075)	2.688 (0.016)
tri-vacancy	4.790 (0.646)	5.285 (0.587)	
tetra-vacancy	6.479 (0.768)	7.097 (0.733)	4.956 (0.451)
hexa-vacancy	8.378 (2.493)	9.210 (2.534)	6.865 (1.245)
[001] SI dumbbell	3.196	3.647	4.135

TABLE XVI: Formation energies, E_f , in eV, for the vacancy, the most stable di-, tri-, tetra- and hexa-vacancy clusters, as found by Klaver *et al.*⁴⁸ and the [001] SI dumbbell in afmD and afmI Fe and in Ni. Total binding energies, E_b , in eV, are given for the vacancy clusters in brackets below the formation energies. The results in Fe are consistent with those found previously⁴⁸. Results in Ni compare well to other DFT calculations^{21,22,47,88,89}. Eshelby corrections were found to be negligible except for the tetra-vacancy in Ni at -0.03 eV, the hexa-vacancy at -0.06 -0.03 and -0.05 eV in afmD Fe, afmI Fe and Ni, respectively, and the dumbbell at -0.05, -0.08 and -0.10 eV in afmD Fe, afmI Fe and Ni, respectively. The only non-negligible effect on binding energies was for the hexa-vacancy, where increases of 0.05 eV, 0.03 and 0.03 eV apply in afmD Fe, afmI Fe and Ni, respectively.

A. Vacancy - solute interactions

We present the formation and binding energies for configurations containing a single vacancy and solute atom, at up to 2nn separation, in Table XVII.

1. V-He binding

We observe strong binding of between 0.60 and 0.66 eV for V-Sub He pairs at 1nn in both Fe reference states. This is significantly greater than the binding between vacancy pairs⁴⁸ and represents the simplest case of enhanced vacancy binding by He, as we will discuss in what follows. We find that He does not remain on-lattice at 1nn to a vacancy but relaxes to a position, best described as, at the centre of a divacancy. With this perspective, the V-Sub He binding represents the significant energetic preference of He for the greater free volume available at the centre of a divacancy over a single vacancy. At 2nn,

A-B/Config.	afmD Fe		afmI Fe	
	E_f	E_b	E_f	E_b
V-sub He/1a	5.216	0.620	5.519	0.623
V-sub He/1b	5.221	0.615	as V-sub He/1c	
V-sub He/1c	5.180	0.656	5.538	0.604
V-sub He/2a	5.940	-0.103	6.293	-0.151
V-sub He/2b	5.854	-0.018	as V-sub He/2c	
V-sub He/2c	5.919	-0.083	6.253	-0.111
V-tetra He/Sub.	4.024	2.251	4.185	2.740
V-tetra He/2a	6.328	-0.053	as V-tetra He/2b	
V-tetra He/2b	6.408	-0.133	6.932	-0.008
V-tetra He/2c	6.377	-0.101	as V-tetra He/2d	
V-tetra He/2d	6.233	0.042	6.883	0.041
V-C/Sub.	-6.981	-0.004	-6.244	-0.655
V-C/1a	-7.165	0.180	-7.276	0.377
V-C/1b	-7.040	0.056	as V-C/1c	
V-C/1c	-7.268	0.283	-7.186	0.287
V-C/2a	-7.031	0.046	as V-C/2b	
V-C/2b	-7.018	0.033	-6.948	0.049
V-N/Sub.	unstable		-5.153	-1.510
V-N/1a	-7.230	0.440	-7.275	0.612
V-N/1b	-7.065	0.275	as V-N/1c	
V-N/1c	-7.217	0.427	-7.161	0.498
V-N/2a	-6.887	0.097	as V-N/2b	
V-N/2b	-6.883	0.092	-6.769	0.106

TABLE XVII: Formation and binding energies in eV for vacancy (species A) to substitutional He, tetra He and octa C/N (species B) with configurations labelled as in Figs. 4, 9 and 10, respectively. Configurations with a single solute atom in the substitutional position (Sub.), where stable, are also considered as an interstitial solute interacting with a vacancy. In afmD Fe, the vacancy-tetra He binding energies were calculated relative to tetra ud He. Binding energies between octa C and N solutes and a vacancy at 3nn and 4nn separations were investigated but did not exceed 0.03 eV. The only non-negligible Eshelby corrections found were for the binding energies between a vacancy and interstitial solutes at no more than 0.02 eV in magnitude.

the interactions are repulsive, at around -0.1 eV, which is slightly greater than that observed between vacancy pairs⁴⁸. He remains on-lattice in these configurations, which explains the lack of enhanced binding at 2nn separation. The situation in Ni is very similar, where we find binding energies of 0.356 eV and -0.127 eV at 1nn and 2nn, respectively.

Interstitial He binds strongly to a vacancy to form a substitutional He configuration. The same is also true in Ni, where we find a binding energy of 2.627 eV, in good agreement with previous work²². Configurations with tetra He at 1nn to a vacancy are unstable. At 2nn, however, we find stable configurations with weak repulsive or attractive binding, depending on the con-

figuration. The fact that no stable configurations were found with tetra He at up to 2nn from a substitutional He atom demonstrates that the addition of a single He to a vacancy significantly increases the capture radius for interstitial He. We expect this effect to increase with the subsequent addition of He, given the additional pressure and dilatation that would be exerted on the surrounding lattice.

2. V-C and V-N binding

C binds to a vacancy by up to 0.38 eV at 1nn in the Fe reference states and weakly at 2nn. This level of binding agrees well with previous experimental and theoretical work in austenite and austenitic alloys⁴³. We find that V-N binding is significantly stronger than for C with binding energies in the range from 0.3 to 0.6 eV at 1nn and around 0.1 eV at 2nn. For both C and N, the substitutional configuration is strongly disfavoured. As discussed in Section III, the substitutional C and N configurations in afmD Fe were found to be unstable and the configuration labelled V-C/Sub in Table XVII has C in a stable position off-lattice by 0.77 Å. Overall, these results bear a strong similarity to those found in bcc Fe³⁴, where binding energies of 0.47 and 0.71 eV were found for C and N at 1nn to a vacancy, respectively.

Results in Ni are broadly similar to those in Fe. We find a V-C binding energy of 0.062 eV at 1nn and 0.121 eV at 2nn. V-N binding is, again, stronger, than C, with energies of 0.362 eV and 0.165 eV at 1nn and 2nn, respectively. We also find a strong repulsion from the substitutional site. We note that the V-C binding at 1nn seems anomalously low, given the other results but no problems were found with this calculation and other test calculations found the same stable structure and energy.

The significant V-C and V-N binding energies suggest that the relatively less mobile solutes could act as vacancy traps, much as was found in bcc Fe^{1,2,37,90}. This would certainly be the case if dissociation of the complex was required before the vacancy could freely migrate but the possibility of cooperative migration also exists. In the fcc lattice there are many possible migration pathways that would avoid the dissociation of this complex, including some that would maintain a 1nn separation. A complete study of these possibilities is beyond the scope of this work but preliminary calculations in Ni show that the energy barriers for C and N jumps that would maintain a 1nn separation to the vacancy are around half the value for the isolated solutes at around 0.75 eV. In contrast, vacancy jumps that maintain a 1nn separation were found to be significantly higher than those for the isolated vacancy but jumps from 1nn to 2nn separation and back exhibited lower or comparable energy barriers. Whilst these calculations are preliminary, they do indicate the distinct possibility of cooperative vacancy-solute motion that would avoid dissociation of the complex. The implications for an absence of vacancy pinning and for the

enhanced diffusion of C and N solutes in the presence of vacancies in austenitic alloys makes this an interesting subject for further study.


B. Vacancy - solute clustering

Small Vacancy-He ($V_m\text{He}_n$) clusters have been found to be highly stable both experimentally^{8,9,11,12} and using DFT techniques^{19,22-25,28} in a number of metals and are, therefore, critically important as nuclei for void formation. Experimental evidence in bcc Fe^{1,2} has also shown that C can act as a vacancy trap through the formation of small, stable $V_m\text{C}_n$ clusters, which has been confirmed in a number of DFT studies^{31,34-37}. Small $V_m\text{N}_n$ clusters have also been shown to exhibit similar stability³⁴.


In this section we present the results of a large number of DFT calculations to find the most stable $V_m\text{X}_n$ clusters, where X is He, C or N, in afmD and afmI Fe. A comprehensive search for the most stable configuration was only practicable for the smaller clusters. For larger clusters, a number of distinct initial configurations, based around the most stable smaller clusters, were investigated to improve the likelihood that the most stable arrangement was found. The total binding energies for the most stable configurations can be found in Table XVIII.

1. $V_m\text{He}_n$ clusters


The geometries of the relaxed $V_m\text{He}_n$ clusters were constrained by the tendency to maximise He-He and He-Fe separations within the available volume and, therefore, minimise the repulsive interactions. In a single vacancy we found that this led to the following structures: two He formed dumbbells centred on the vacancy with He-He bond lengths around 1.5 Å; three He formed a near-equilateral triangle with bond lengths of between 1.6 and 1.7 Å; four He formed a near-regular tetrahedron with bond lengths between 1.6 and 1.7 Å; five He formed a near-regular triangular bipyramid with bond lengths between 1.6 and 1.8 Å and six He formed a near-regular octahedron with bond lengths between 1.6 and 1.8 Å. In clusters with more than one vacancy, a single He atom relaxed to a central position. Additional He tended to form similar clusters to those seen in a single vacancy but now around the centre of the vacancy cluster. The tri-vacancy case is interesting because previous DFT calculations in austenite⁴⁸ found that a configuration consisting of a tetrahedral arrangement of vacancies with one Fe atom near the centre of the void, which can be considered as the smallest possible stacking fault tetrahedron (SFT), was more stable than the planar defect of three vacancies with mutual 1nn separations. The addition of a single He atom was enough to reverse the order of stability with a difference in the total binding energy of 0.8 eV in afmI Fe, in favour of the planar defect. We suggest that this result should readily generalise, with planar defects

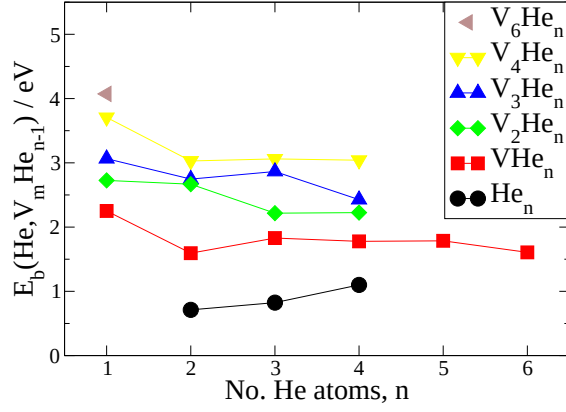


(a) afmD Fe, He binding

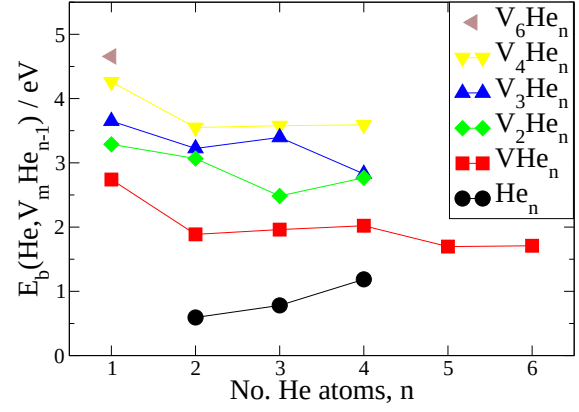


(b) afmI Fe, He binding

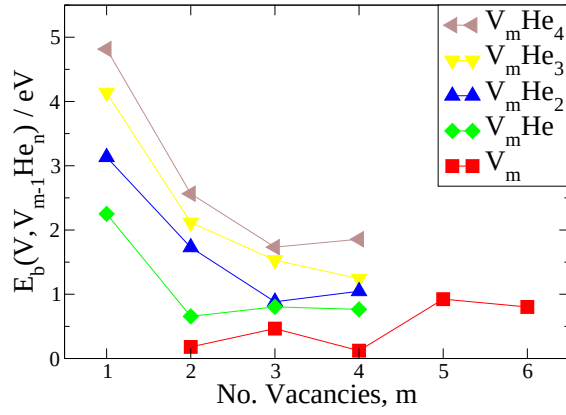


(c) afmD Fe, V binding

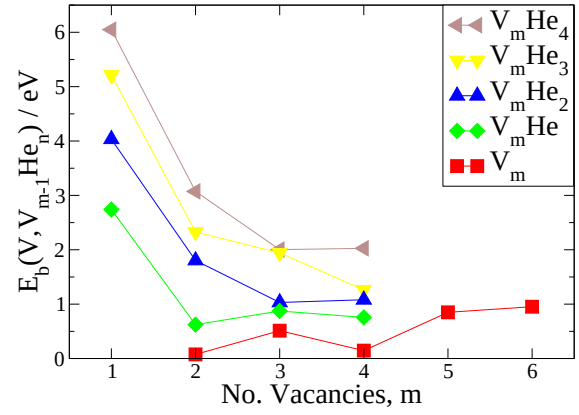

(d) afmI Fe, V binding

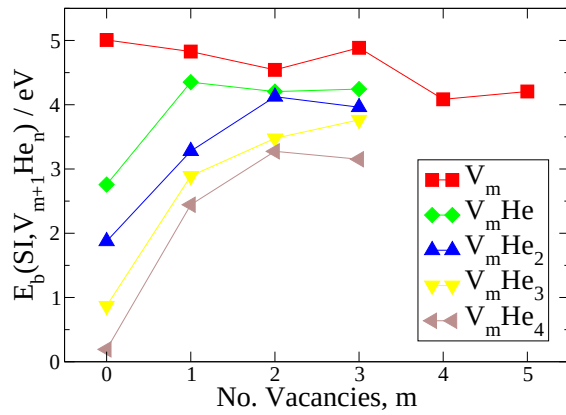

(e) afmD Fe, SI binding

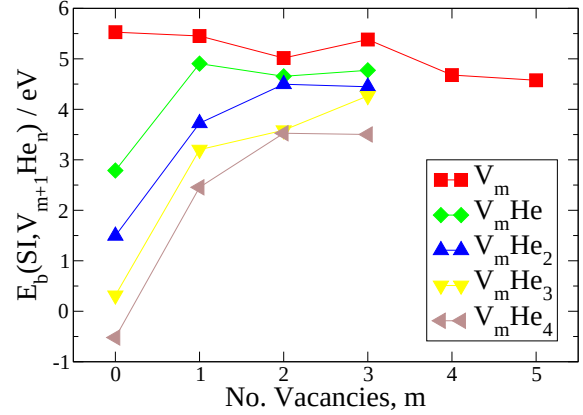

(f) afmI Fe, SI binding

FIG. 11: Binding energies, in eV, for a He atom, V or SI to an existing cluster to form one with the $V_m\text{He}_n$ stoichiometry in afmD Fe (figures (a), (c) and (e)) and afmI Fe (figures (b), (d) and (f)) Fe. Interstitial He cluster data has been included in figures (a) and (b) for completeness.

Cluster	afmD Fe E_b	afmI Fe E_b	Cluster	afmD Fe E_b	afmI Fe E_b	Ni E_b
VHe	2.251	2.740	VC	0.283	0.377	0.121
VHe ₂	3.845	4.627	VC ₂	0.484	0.795	0.422
VHe ₃	5.674	6.588	VC ₃	0.423	0.484	-0.206
VHe ₄	7.452	8.609	V ₂ C	0.499	0.550	0.211
VHe ₅	9.239	10.305	V ₄ C	1.107	1.307	0.718
VHe ₆	10.845	12.015	V ₆ C	3.546	3.253	1.531
V ₂ He	2.907	3.363	VN	0.440	0.612	0.362
V ₂ He ₂	5.575	6.430	VN ₂	0.981	1.295	0.872
V ₂ He ₃	7.791	8.990	VN ₃	1.264	1.341	0.877
V ₂ He ₄	10.197	11.682	VN ₄	1.371	1.514	0.933
V ₃ He	3.711	4.237	VN ₅	1.439	1.516	0.651
V ₃ He ₂	6.458	7.461	VN ₆	1.474	1.482	0.246
V ₃ He ₃	9.323	10.857	V ₂ N	0.743	0.933	0.558
V ₃ He ₄	11.750	13.685	V ₄ N	1.364	1.573	1.047
V ₄ He	4.475	4.993	V ₆ N	3.224	3.466	2.033
V ₄ He ₂	7.504	8.542				
V ₄ He ₃	10.565	12.120				
V ₄ He ₄	13.606	15.711				
V ₆ He	6.566	7.191				

TABLE XVIII: Total binding energies, E_b , in eV for the most stable V_mX_n clusters found in afmD and afmI Fe, where X is He, C or N. Results in Ni are also given for C and N and can be found in the literature for He^{19,22}. Eshelby corrections to E_b for $V_m\text{He}_n$ clusters were found to be below 0.05 eV in magnitude except for VHe₅ and $V_m\text{He}_n$ with m and n equal to 3 or 4, which were below 0.1 eV and VHe₆, which was 0.2 eV. For C and N clusters, the corrections were below 0.02 eV in magnitude except for those with six vacancies or with four or more N atoms, where the corrections were up to 0.1 eV for most but were 0.2 eV for VN₆ in afmI Fe and VN₅ in Ni and 0.3 eV for VN₆ in Ni.

being more stable than SFTs with sufficient addition of He. That said, however, planar defects have been found⁴⁸ to be less stable than three-dimensional proto-voids and this situation is unlikely to change with the addition of He due to the greater free volume of the latter clusters.

In Section III A 1 the addition of a single He to a vacancy was found to have very little effect on the local magnetism. The addition of He to vacancy clusters was generally found to have very little effect on the total magnetic moment of the supercells containing the cluster. The only exception was for the single vacancy in afmD Fe, although it took the addition of six He atoms to significantly change the magnetic moment. Even in the absence of vacancies, a cluster of at least three He atoms was necessary to influence the total magnetic moment.

In Fig. 11 we present results for the binding energy of either a He atom, vacancy (V) or [001] self-interstitial dumbbell (SI) to an already existing cluster to form one with the $V_m\text{He}_n$ stoichiometry. These results show that He consistently binds strongly to an existing cluster and

that the strength of the binding only increases with m . For a fixed value of n , this binding energy will converge to the formation energy for interstitial He [see Table I] as m increases and is well on the way to doing that for $n = 1$. For fixed m the additional He binding energy appears to plateau as n increases although it should diminish eventually as the pressure within the cluster builds.

The binding energy for an additional vacancy is also, consistently, positive. The presence of He significantly increases this additional binding for all values of m , which is consistent with the observation that it aids the nucleation, stabilisation and growth of voids in irradiated environments^{10,13–16}. For fixed n , the data shows that the vacancy binding energy is tending to a plateau as m increases and is consistent with the fact that all of these curves should converge to the vacancy formation energy.

The SI binding energy can be related to the vacancy binding energy as follows,

$$E_b(\text{SI}, V_{m+1}\text{He}_n) = E_f(\text{SI}) + E_f(\text{V}) - E_b(\text{V}, V_m\text{He}_n), \quad (9)$$

which implies that the spontaneous emission of an SI from an existing cluster will be energetically favourable if and only if the binding of the newly created vacancy is greater than the Frenkel pair formation energy. The data shows that the SI binding energy clearly decreases as He concentration is increased at fixed m and for sufficiently high concentration will become negative. Indeed, it is energetically favourable for an interstitial He cluster with four He atoms in afmI Fe, and most likely for five He atoms in afmD Fe, to spontaneously emit an SI defect. This mechanism was proposed to explain the observation of He bubbles in Au samples after sub-threshold He implantation⁸³ and could also explain observations of He trapping in Ni⁹¹, where the He was introduced by natural tritium decay to avoid implantation-produced defects. Our results show that this would, most likely, occur in austenite and austenitic alloys and could lead to bubble formation, with the potential for blistering in the presence of, even low-energy, bombardment by He ions, as seen in W^{92,93}.

As a whole, the binding energy data is qualitatively similar to DFT results in Al²³ and Pd²⁴ and is quantitatively similar to results in bcc Fe²⁵ and Ni^{19,22}. This observation gives us confidence that our results are, not only, applicable to austenite but to austenitic alloys more generally.

The binding energy data above has also been used to determine the dissociation energy, that is the energy of emission, of He, V or SI from a $V_m\text{He}_n$ cluster using the simple ansatz that the dissociation energy, $E_{\text{diss.}}(\text{X})$, for species, X, is given by

$$E_{\text{diss.}}(\text{X}) = E_b(\text{X}) + E_m(\text{X}), \quad (10)$$

where $E_m(\text{X})$ is the migration energy for isolated species, X. We present results for the dissociation energies in Fig. 12, using the migration energies in Table XIX.

There is a strong and distinct dependence on the He to vacancy ratio, n/m , for the dissociation energies of

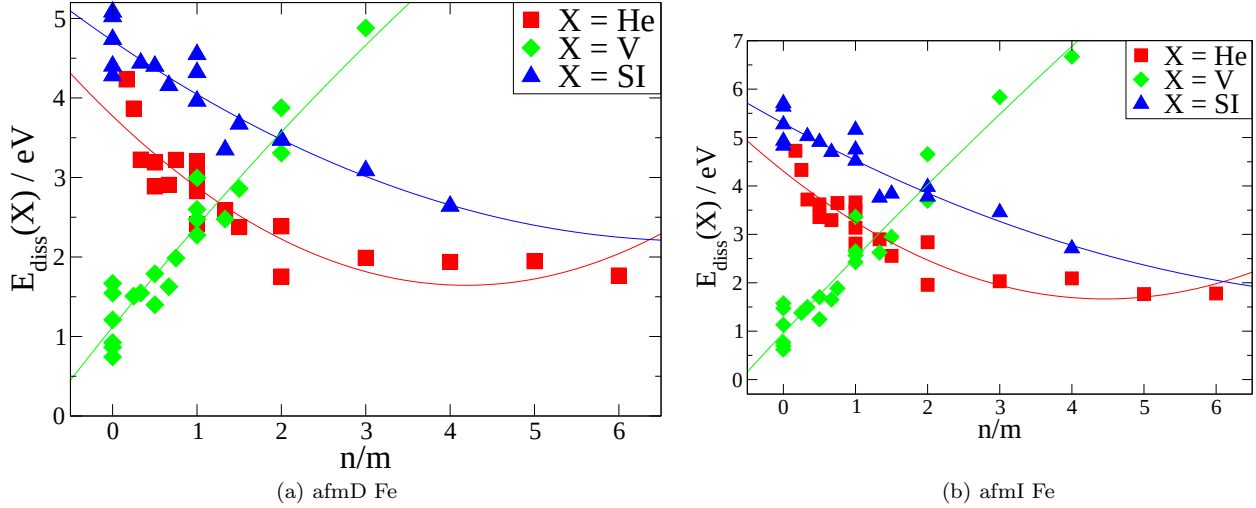


FIG. 12: Dissociation energies, $E_{\text{diss.}}(X)$, in eV, for species X from a $V_m\text{He}_n$ cluster, where X is a He, V or SI. Results are presented for (a) afmD Fe and (b) afmI Fe versus the He to vacancy ratio, n/m . The solid curves are simple polynomial fits to the data and are present to aid visualisation.

Species, X	afmD Fe	afmI Fe
He	0.160	0.070
V	0.743	0.622
SI	0.196	0.254

TABLE XIX: Migration energies, $E_m(X)$, in eV, for Species, X, where X is He, V or SI. For He, the lowest values from Table VII were used. For V, the lowest vacancy migration energies from Klaver *et al.*⁴⁸ were used. The SI migration energies were calculated here as that for a [100] dumbbell SI migrating between two lattice sites at 1nn separation within a magnetic plane using identical settings to Klaver *et al.*⁴⁸

the three species. Both graphs exhibit a clear crossover between the He and V curves at around $n/m = 1.3$ and another between the He and SI curves at about $n/m = 6$. An identical He-V crossover ratio was found in bcc Fe²⁵ and fcc Al²³. For n/m below 1.3 the clusters are most prone to emission of a vacancy, between 1.3 and 6 He has the lowest dissociation energy and above 6 SI emission is the preferred dissociation product. The slope of the curves ensures that emission of the species with the lowest dissociation energy will make the resulting cluster more stable. At sufficiently high temperatures that these processes are not limited by kinetics this should lead to the formation of the most stable clusters, which have an n/m value at the He-V crossover, where our results predict a minimum dissociation energy of around 2.8 eV in both afmD and afmI Fe.

2. V_mC_n and V_mN_n clusters

In fct afmD and afmI Fe and in Ni we considered VX_n clusters with octa-sited C and N at 1nn to the vacancy and configurations where C and N are close enough to form C-C and N-N bonds within the vacancy. Our results for VC_2 and VN_2 clusters are given in Table XX. We found that VX_2 clusters with octa-sited C and N are most stable when the C/N atoms are as far apart as possible, that is, opposite one another across the vacancy. For these configurations the total binding energy is more than the sum of the binding energies for each single solute to the vacancy, indicating either some chemical or cooperative strain interaction. We found that C-C dumbbells centred on the vacancy are stable, with bond lengths between 1.38 and 1.48 Å, that is, much shorter than the separations between octahedral sites. The most stable lie along $\langle 100 \rangle$ directions and binding over and above that for octa sited C was found in afmD Fe and Ni. The enhancement in binding upon forming a C-C dumbbell is not, however, as pronounced as was seen in bcc Fe^{25,34–36}. We also found stable configurations with N-N dumbbells in Fe and Ni with bond lengths between 1.34 and 1.49 Å, although they exhibit a much lower, and generally negative, total binding energy compared to configurations with octa sited N atoms.

For VX_3 clusters, we investigated all possible configurations with three octa-sited C or N solutes in addition to those with a C-C dumbbell and an octa-sited C solute in one of the four octa sites perpendicular to the dumbbell axis and a configuration with three C atoms close enough for C-C bonding. Although we do find stable configurations with C-C bonding in either a dumbbell or triangular arrangement in both Fe and Ni, these arrangements

Config.	afmD Fe		afmI Fe		Ni	
	E_f	E_b	E_f	E_b	E_f	E_b
VC ₂ clusters						
1a-1a (opp.)	-16.226	0.444	-16.551	0.795	-15.692	0.199
1b-1c	-16.166	0.385	-16.466	0.711	as 1a-1a (opp.)	
1a-1a (adj.)	-15.908	0.127	-16.163	0.408	-15.396	-0.097
1a-1b	-15.832	0.050	-16.116	0.361	as 1a-1a (adj.)	
1a-1c	-16.104	0.323	as 1a-1b		as 1a-1a (adj.)	
[100] dumb.	-16.087	0.305	-16.224	0.469	-15.915	0.422
[001] dumb.	-16.265	0.484	-16.262	0.507	as [100] dumb.	
[110] dumb.	-15.407	-0.375	-15.238	-0.517	-15.380	-0.113
[111] dumb.		rlx [001]	dumb.		-15.565	0.072
VN ₂ clusters						
1a-1a (opp.)	-16.373	0.981	-16.579	1.295	-14.559	0.872
1b-1c	-16.124	0.732	-15.932	0.648	as 1a-1a (opp.)	
1a-1a (adj.)	-16.113	0.720	-16.237	0.953	-14.279	0.591
1a-1b	-16.051	0.658	-16.037	0.753	as 1a-1a (adj.)	
1a-1c	-16.228	0.835	as 1a-1b		as 1a-1a (adj.)	
[100] dumb.	-14.451	-0.942	-14.487	-0.796	-13.616	-0.071

TABLE XX: Formation and total binding energies, in eV, for the interactions of a vacancy with two octa sited C or N solutes. Configurations with C or N in octa sites at 1nn to the vacancy are labelled by the positions of the two solutes as in Fig. 10. When both octa solutes are in the same plane as the vacancy the configurations are additionally labelled by their relative orientation i.e. opposite (opp.) or adjacent (adj.) to one another. Doubly mixed dumbbells centred on the vacancy site were also considered as configurations of an interacting vacancy with two octa solutes and the total binding energies were calculated accordingly. Eshelby corrections to both E_f and E_b were found to be no more than 0.03 eV in magnitude.

are the least stable and exhibit significant, negative total binding energies. The most stable arrangements consist of three octa sited C atoms placed as far apart as possible, for example in three 1a sites relative to the vacancy as in Fig. 10. However, the total binding energies for the most stable VC₃ clusters [see Table XVIII] are less than for VC₂, which implies that a vacancy can only bind up to two C atoms within a vacancy. A vacancy may still, however, bind more than at 2nn octa sites but we did not investigate this possibility due to the strongest binding being at 1nn to the vacancy and due to the large number of possible configurations.

The most stable VN₃ clusters have the same geometry as found with C but, in contrast, are more stable than VN₂ clusters. Beyond this point, we found that the total binding energy only increases for up to four N atoms in afmI Fe and Ni but increases all the way up to six N atoms in afmD Fe. That said, however, the binding energy per N atom only increases up to a VN₂ cluster in all reference states. The equilibrium concentrations of clusters with more than two N atoms, which can be calculated using the law of mass-action³⁷, would very likely be negligible,

even at room temperature. Despite their magnitude, the Eshelby corrections do not change these conclusions but would result in the total binding energy increasing all the way up to six N atoms in afmI Fe, as was found for afmD Fe.

We investigated site preference and binding for single C and N solutes to the most stable di-, tetra- and hexa-vacancy clusters in afmD and afmI Fe and in Ni. For the V₂C cluster in afmD Fe, we considered all 1nn octa sites to the three distinct types of 1nn di-vacancy as well as configurations with C at the centre of all 1nn and 2nn di-vacancy clusters. For the octa sites, C was found to bind to existing di-vacancy clusters with similar binding energies to a single vacancy, that is with $E_b(C, V_2)$ in the range from 0.03 to 0.32 eV. The most stable of these, which was also found to be the most stable V₂C cluster, contained the most stable di-vacancy and bound C more stably than to a single vacancy. We found that C was repelled from the centre of a 1nn di-vacancy lying within a magnetic plane but bound to the other two 1nn di-vacancies with similar energies to those found in octa sites. As in bcc Fe^{31,35,36}, the most preferred site for C was at the centre of a 2nn di-vacancy, with $E_b(C, V_2) = 0.35$ eV. However, this was not sufficient to overcome the difference in stability between 1nn and 2nn di-vacancies in afmD Fe⁴⁸ and did not, therefore, form them most stable V₂C cluster, in contrast to in bcc Fe.

The analysis above motivated the use of only the most stable 1nn di-vacancy in the remaining calculations along with configurations containing solutes at the centre of 2nn di-vacancies. For N in afmD Fe, the order of site preference mirrors that for C. An N solute is capable of stabilising a 2nn di-vacancy configuration but the most stable V₂N cluster shared the same geometry as for C with a binding energy to the underlying di-vacancy of 0.56 eV, which is, again, in excess of the binding to a single vacancy.

The situation in afmI Fe and Ni was found to be rather similar to that of afmD Fe. For both C and N, the site at the centre of a 1nn (in-plane) di-vacancy was disfavoured. The most stable configuration generally contained an octa-sited solute bound to a 1nn di-vacancy. The only exception was in afmI Fe, where a configuration with C at the centre of a 2nn di-vacancy lying within a magnetic plane had a greater total binding energy but only by 0.03 eV. This, most likely resulted from the much smaller energy difference between 1nn and 2nn di-vacancies in afmI Fe of compared to afmD Fe⁴⁸ and to Ni, where we find an energy difference of 0.1 eV in favour of the 1nn di-vacancy. In the most stable clusters, the binding of the solutes to the underlying di-vacancy was, once again, in excess of the binding to a single vacancy.

For the binding of C and N to the most stable tetra-vacancy, we found that the central position was extremely disfavoured. We investigated all configurations with solute atoms in an octa site at 1nn to at least a single vacancy. We also performed calculations with solute atoms placed initially at random within the proto-void

but found that these relaxed to octa sites already considered. Configurations with only a single vacancy at 1nn to the solute were found to be the most stable. The total binding energies for these configurations are given in Table XVIII. Using these results we found that the binding of C and N to the tetra-vacancy was in excess of that to a di-vacancy and a single vacancy, in all cases except for N in afmI Fe, where the binding to the tetra-vacancy and di-vacancy reversed order, although they only differ by 0.02 eV.

For the hexa-vacancy, the central octa site was unstable for both C and N in afmD Fe. In afmI Fe and Ni it was stabilised by symmetry but still strongly disfavoured. This repulsion is, however, significantly less than was observed for the tetra-vacancy. Closer observation showed that while the nearest neighbouring Fe and Ni atoms to the solutes moved very little under relaxation in the tetra-vacancy, the contraction in bond length was between 25 and 30 % in the hexa-vacancy from an initial separation of around 3 Å. This demonstrates how important the formation of strong chemical bonds with characteristic bond lengths is to the stability of configurations containing C and N in Fe and Ni.

We investigated the stability of configurations with C and N in all octa sites at 1nn to at least one vacancy in the hexa-vacancy cluster. We found that there were additional stable sites, lying along $\langle 100 \rangle$ axes projected out from the centre of the hexa-vacancy. For C, these sites were found to lie between the first vacancy reached along these axes and the next octa site out. They are close to but distinct from the octa sites and we, therefore, refer to them as octa-b sites. For N, stable sites were found between the centre of the hexa-vacancy and the first vacancy reached along the $\langle 100 \rangle$ axes and we refer to these as off-centre sites. We found that C was, consistently, most stable in an octa-b site whereas N preferred octa sites with two vacancies at 1nn, although an off-centre site along $[00\bar{1}]$ was the most stable in afmD Fe.

Once again, the binding energy between the solutes and hexa-vacancy was greater than for all smaller vacancy clusters. We summarise these results for $E_b(X, V_m)$ in Fig. 13, which clearly shows the increase in binding energy as the vacancy cluster becomes larger. It also clearly shows that in the same reference state, the binding energy for N is consistently greater than for C and that the binding energies in afmI Fe lie above those in afmD Fe. The one anomalous point is the binding energy for C to a hexa-vacancy in afmD Fe, which is much larger than the trends would suggest. Other configurations with C in an octa-b site in afmD Fe exhibited similar levels of binding and no problems with any of these calculations or instabilities in the relaxed structures could be found.

C. $[001]$ dumbbell SI - solute interactions

We investigated the binding of He, C and N solutes to a $[001]$ dumbbell in afmD and afmI Fe and in Ni and

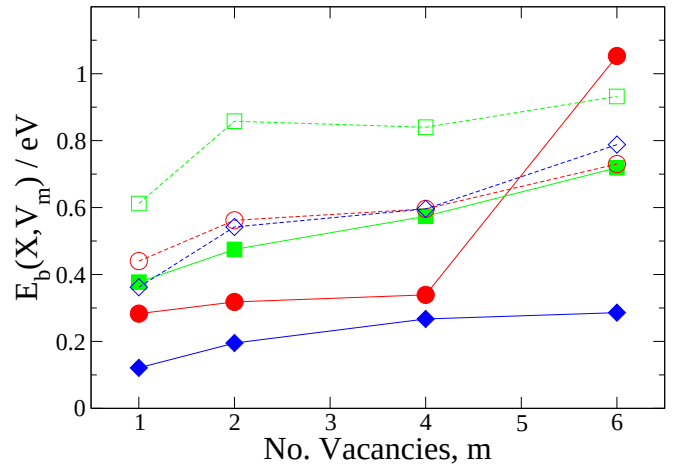


FIG. 13: Binding energy, $E_b(X, V_m)$, in eV, where X is C (filled symbols and solid lines) or N (unfilled symbols and dashed lines) in afmD Fe (red circles), afmI Fe (green squares) and Ni (blue diamonds). The binding energies were calculated for the most stable clusters.

present the results in Table XXI.

We found that interstitial He, placed initially 1nn to a $[001]$ SI dumbbell, either spontaneously displaced under relaxation to a 2nn site or exhibited a repulsive binding energy in Fe. At 2nn, however, a positive binding energy was observed, up to almost 0.2 eV, as was found in Ni^{19,22}. Eshelby corrections do not qualitatively change these results and would only act to enhance the binding at 2nn. This positive binding energy is comparable to that in bcc Fe²⁵ but while significant, it is only likely to result in mutual trapping at low temperature, given the high mobility of the two species. Taken as a model for the binding of interstitial He to other overcoordinated defect sites, such as near dislocations and grain boundaries, however, this result does show that He would be likely to be trapped at such sites, leading to interstitial He cluster formation and spontaneous bubble nucleation and growth, as discussed earlier. It is worth mentioning that bubble nucleation by this mechanism would happen much more readily at grain boundaries where, due to their disorder, vacancies can be formed without the additional SI.

A substitutional He atom in the 1b and 1c sites [see Fig. 4] to a $[001]$ SI dumbbell resulted in the spontaneous recombination of the vacancy and SI and the kick-out of an interstitial He atom. At all other 1nn and 2nn sites except 2b in Ni, however, stable complexes with binding energies of up to around 0.2 eV were formed. Barriers to recombination for these complexes, while positive, were not calculated in this work. These results do, however, show that substitutional He, and most likely, other $V_m\text{He}_n$ clusters can act as trapping sites for SI dumbbells in austenite and austenitic alloys with a capture radius extending out to at least 2nn. We can also speculate that, once trapped, recombination will be likely to occur.

A-B/Config.	afmD Fe		afmI Fe		Ni	
	E_f	E_b	E_f	E_b	E_f	E_b
[001]-tetra He/1a	unstable		unstable			
[001]-tetra He/1b	7.734	-0.075	as 1a			
[001]-tetra He/2a	7.494	0.166	8.517	0.098		
[001]-tetra He/2b	7.761	-0.036	as 2a			
[001]-tetra He/2c	7.609	0.117	8.435	0.180		
[001]-tetra He/2d	7.514	0.146	as 2c			
[001]-sub He/1a	7.045	0.176	7.743	0.089	7.085	0.235
[001]-sub He/2a	7.164	0.057	7.815	0.017	7.316	0.003
[001]-sub He/2b	7.050	0.171	7.653	0.179	unstable	
[001]-sub He/2c	7.095	0.126	as 2b		as 2b	
[001]-C/1a	-5.563	-0.037	-5.007	-0.202	-4.300	0.012
[001]-C/1b	-4.604	-0.997	-3.975	-1.234		
[001]-C/1c	-4.459	-1.141	as 1b			
[001]-C/2a	-5.585	-0.015	-5.064	-0.145	-4.322	0.034
[001]-C/2b	-5.527	-0.074	as 2a		as 2a	
[001]-C/4a	-5.626	0.025	-5.266	0.057	-4.303	0.015
[001]-C/4b	-5.652	0.051	-5.287	0.078	-4.362	0.075
[001]-C/4c	-5.642	0.041	as 4b		as 4b	
[001]-N/1a	-5.106	-0.300	-4.444	-0.529	-3.198	-0.188
[001]-N/1b	-4.461	-0.945	-3.721	-1.252		
[001]-N/1c	-4.197	-1.209	as 1b			
[001]-N/2a	-5.290	-0.116	-4.762	-0.211	-3.400	0.015
[001]-N/2b	-5.251	-0.155	as 2a		as 2a	
[001]-N/4a	-5.425	0.019	-5.027	0.054	3.402	0.017
[001]-N/4b	-5.430	0.024	-5.043	0.069	-3.481	0.096
[001]-N/4c	-5.458	0.052	as 4b		as 4b	

TABLE XXI: Formation and binding energies in eV for [001] self-interstitial dumbbell (species A) - solute (species B) interactions. For octa-sited C and N solutes the configurations are labelled as in Fig. 10. He interactions were investigated with He sited substitutionally and tetrahedrally with configurations labelled as in Figs. 4 and 9, respectively. Configurations with substitutional He in 1b and 1c positions relative to a [001] dumbbell SI were unstable to defect recombination and interstitial He kick-out. In Ni, the [001]-tetra He binding energy was observed to be 0.20 eV²². Eshelby corrections were found down to -0.1 eV for configurations containing substitutional He but the related increases in E_b were no more than 0.02 eV. For configurations containing interstitial solutes E^{corr} could be as low as -0.2 eV with corresponding increases in E_b up to 0.08 eV.

Both C and N are either repelled from 1nn and 2nn sites to a [001] SI dumbbell or show very little positive binding, much as was observed in bcc Fe³⁴. Eshelby corrections do not change this conclusion in Fe but would result in binding of around 0.1 eV at 2nn in Ni. Motivated by the result that C does exhibit positive binding to the most stable SI and small SI clusters in bcc Fe¹⁹ at further separation, we investigated this possibility here and found sites with binding energies from 0.05 to 0.1 eV

at 4nn to the dumbbell, which would only be enhanced by Eshelby corrections. These sites can be related to the corresponding ones in bcc Fe by a Bain transformation⁹⁴ and the binding almost certainly results from strain field effects in both cases. The fact that such binding was found to increase with interstitial cluster size¹⁹ means that Cottrell atmospheres³ of C and N are very likely to form around other overcoordinated defects, such as dislocations and grain boundaries, in both ferritic and austenitic alloys under conditions where these species are mobile.

V. CONCLUSIONS

An extensive set of first-principles DFT calculations have been performed to investigate the behaviour and interactions of He, C and N solutes in austenite, dilute Fe-Cr-Ni alloys and Ni as model systems for austenitic steel alloys. In particular, we have investigated the site stability and migration of single He, C and N solutes, their self-interactions, interactions with substitutional Ni and Cr solutes and their interactions with point defects typical of irradiated environments, paying particular attention to the formation of small $V_m X_n$ clusters.

Direct comparison with experiment verifies that the two-state approach used to model austenite in this work is reasonably predictive. Overall, our results demonstrate that austenite behaves much like other fcc metals and is qualitatively similar to Ni in many respects. We also observe a strong similarity between the results presented here for austenite and those found previously for bcc Fe.

We find that interstitial He is most stable in the tetrahedral site and migrates via off-centre octahedral transition states with a migration energy from 0.1 to 0.2 eV in austenite and 0.13 eV in Ni. The similarity of these results and the weak interactions with Ni and Cr solutes in austenite suggests a migration energy in Fe-Cr-Ni austenitic alloys in the 0.1 to 0.2 eV range. Interstitial He will, therefore, migrate rapidly from well below room temperature until traps are encountered. Its strong clustering tendency, with an additional binding energy approaching 1 eV per He atom in austenite and 0.7 eV in Ni, will lead to a reduction in mobility as interstitial He concentration increases. Interactions with overcoordinated defects, which are on the order of a few tenths of 1 eV, will result in the build up and clustering of interstitial He at dislocations and grain boundaries. The most stable traps, however, are vacancy clusters and voids, with binding energies of a few eV. The strength of this binding means that growing interstitial He clusters eventually become unstable to spontaneous Frenkel pair formation, resulting in the emission of a self-interstitial and nucleation of a $V\text{He}_n$ cluster. The binding of additional He and vacancies to existing $V_m\text{He}_n$ clusters increases significantly with cluster size, leading to unbounded growth and He bubble formation in the presence of He and vacancy fluxes. The most stable clusters have a helium to

vacancy ratio, n/m , of around 1.3, with a dissociation energy for the emission of He and V of 2.8 eV in austenite and Ni. Generally, we assume that $V_m\text{He}_n$ clusters are immobile. For the simplest case of substitutional He, however, migration is still possible. In a thermal vacancy population, diffusion by the dissociative mechanism dominates, with an activation energy of between 0.6 and 0.9 eV in Fe and 1.4 in Ni. In irradiated environments, however, the vacancy mechanism dominates and diffusion can proceed via the formation and migration of the stable $V_2\text{He}$ complex, with an activation energy of between 0.3 and 0.6 eV in Fe and 0.8 eV in Ni.

We find that C and N solutes behave similarly, both in austenite and Ni, although the interactions of N are stronger. The octahedral lattice site is preferred by both solutes, leading to a net expansion of the lattice and a reduction of the c/a ratio in the afmD and afmI Fe reference states. Both solutes also stabilise austenite over ferrite and favour ferromagnetic over antiferromagnetic states in austenite. Carbon migrates via a $\langle 110 \rangle$ transition state with a migration energy of at least 1.3 eV in austenite and of 1.6 eV in Ni. For N, migration proceeds via the crowdion or tetrahedral sites, depending on path, with a migration energy of at least 1.4 eV in austenite and 1.3 eV in Ni. Pairs of solute atoms are repelled at 1nn and 2nn in austenite and do not interact in Ni. Both C and N interact very little with Ni solutes in austenite but bind to Cr, which may act as a weak trap and encourage the formation of Cr-carbonitrides in conditions where the solutes are mobile. Carbon binds to a vacancy by up to 0.4 eV in austenite and 0.1 eV in Ni, with N binding more strongly at up to 0.6 eV in austenite and 0.4 eV in Ni. While this may suggest that C and N act as vacancy traps, as in bcc Fe, preliminary calculations in Ni show that VC and VN clusters may diffuse cooper-

atively with an effective migration energy similar to that for the isolated vacancy. This also raises the possibility of enhanced C and N mobility in irradiated alloys and their segregation to defect sinks. A vacancy can bind up to two C atoms and up to six N atoms in austenite (or four in Ni), although the additional binding energy reduces significantly above two. Covalent bonding was observed between solutes in a vacancy but did not lead to any enhanced stability, as seen in bcc Fe. Both C and N show a strong preference for sites near the surface of vacancy clusters and the binding increases with cluster size, suggesting that they will decorate the surface of voids and gas bubbles, when mobile. A binding energy of 0.1 eV was observed to a [001] SI dumbbell in austenite and Ni, which we would expect to increase with interstitial cluster size, as in bcc Fe, resulting in Cottrell atmospheres of C and N around dislocations and grain boundaries in austenitic alloys.

Along with previous work, these results provide a complete database that would allow realistic Fe-Cr-Ni austenitic alloy systems to be modelled using higher-level techniques, such as molecular dynamics using empirical potentials and kinetic Monte Carlo simulations. As such, they play a critical role in a multi-scale modelling approach to study the microstructural evolution of these materials under irradiation in typical nuclear environments.

VI. ACKNOWLEDGEMENTS

This work was part sponsored through the EU-FP7 PERFORM-60 project, the G8 funded NuFUSE project and EPSRC through the UKCP collaboration.

-
- * Email: dhepburn@ph.ed.ac.uk
† Email: gjackland@ed.ac.uk
- ¹ A. Vehanen, P. Hautojärvi, J. Johansson, J. Yli-Kauppi and P. Moser, *Phys. Rev. B* **25**, 762-780 (1982).
 - ² S. Takaki, J. Fuss, H. Kuglers, U. Dedek and H. Shultz, *Rad. Eff.* **79**, 87-122 (1983).
 - ³ A.H. Cottrell and B.A. Bilby, *Proc. Phys. Soc. A* **62**, 49 (1949).
 - ⁴ C.S. Becquart and C. Domain, *Curr. Opin. Sol. State Mater. Sci.* **16**, 115-125 (2012).
 - ⁵ D. Edwards Jr. and E.V. Kornelsen, *Surf. Sci.* **44**, 1-10 (1974).
 - ⁶ V. Philipps, K. Sonnener and J.M. Williams, *J. Nucl. Mater.* **107**, 271 (1982).
 - ⁷ V. Sciani and P. Jung, *Rad. Eff.* **78**, 87-99 (1983).
 - ⁸ R. Vassen, H. Trinkaus and P. Jung, *Phys. Rev. B* **44**, 4206 (1991).
 - ⁹ A.V. Fedorov, A. van Veen and A.I. Ryazanov, *J. Nucl. Mater.* **233-237**, 385-389 (1996) ; *J. Nucl. Mater.* **258-263** 1396-1399 (1998).
 - ¹⁰ A. van Veen, R.J.M. Konings and A.V. Fedorov, *J. Nucl. Mater.* **320**, 77-84 (2003).
 - ¹¹ X.Z. Cao, Q. Xu, K. Sato and T. Yoshiie, *J. Nucl. Mater.* **412**, 165-169 (2011) ; *J. Nucl. Mater.* **417**, 1034-1037 (2011).
 - ¹² K. Ono, H. Sasagawa, F. Kudo, M. Miyamoto and Y. Hidaka, *J. Nucl. Mater.* **417**, 1026-1029 (2011).
 - ¹³ L.K. Mansur, E.H. Lee, P.J. Maziasz and A.P. Rowcliffe, *J. Nucl. Mater.* **141-143**, 633-646 (1986).
 - ¹⁴ Y. Murase, J. Nagakawa, N. Yamamoto and H. Shiraishi, *J. Nucl. Mater.* **255**, 34-43 (1998).
 - ¹⁵ L. Liu, T. Mitamura, M. Terasawa, A. Yamamoto and H. Tsubakino, *Int. J. Nano.* **3**, 765-773 (2004).
 - ¹⁶ L. Peng, Q. Huang, S. Ohnuki and C. Yu, *Fus. Eng. Des.* **86**, pp2624-2626 (2011).
 - ¹⁷ H. Schroeder, W. Kesternich and Hans Ullmaier, *Nucl. Eng. and Design/Fusion* **2**, 65-95 (1985).
 - ¹⁸ Y. Katoh, M. Ando and A. Kohyama, *J. Nucl. Mater.* **323**, 251-262 (2003).
 - ¹⁹ L. Malerba *et al.*, *J. Nucl. Mater.* **406**, 7-18 (2010).
 - ²⁰ URL: <http://www.perform60.net/>
 - ²¹ X.T. Zu, L. Yang, F. Gao, S.M. Peng, H.L. Heinisch, X.G.

- Long and R.J. Kurtz, Phys. Rev B **80**, 054104 (2009).
- ²² C. Domain and C.S. Becquart, FP7 PERFECT Project Report for deliverable P58, 2007 (unpublished).
- ²³ L. Yang, X.T. Zu and F. Gao, Physica B **403**, 2719-2724 (2008).
- ²⁴ X. Zeng, H. Deng and W. Hu, Nucl. Instrum. Meth. Phys. Res. B **267**, 3037-3040 (2009).
- ²⁵ C.-C. Fu and F. Willaime, Phys. Rev. B **72**, 064117 (2005); J. Nucl. Mater. **367-370**, 244-250 (2007).
- ²⁶ T. Seletskaiia, Yu. Osetsky, R.E. Stoller and G.M. Stocks, Phys. Rev. Lett. **94**, 046403 (2005).
- ²⁷ C.S. Becquart and C. Domain, Phys. Rev. Lett. **97**, 196402 (2006).
- ²⁸ C.S. Becquart and C. Domain, J. Nucl. Mater. **385**, 223-227 (2009).
- ²⁹ C.s. Becquart, C. Domain, U. Sarkar, A. DeBacker and M. Hou, J. Nucl. Mater. **403**, 75-88 (2010).
- ³⁰ P. Zhang, J. Zhao, Y. Qin and B. Wen, J. Nucl. Mater. **413**, 90-94 (2011).
- ³¹ C.J. Ortiz, M.J. Caturla, C.C. Fu and F. Willaime, Phys. Rev. B **75**, 100102(R) (2007); J. Nucl. Mater. **386-388**, 33-35 (2009); Phys. Rev. B **80**, 134109 (2009).
- ³² C.-C. Fu, J. Dalla Torre, F. Willaime, J.-L. Bocquet and A. Barbu, Nat. Mater. **4**, 68 (2005).
- ³³ D.E. Jiang and E.A. Carter, Phys. Rev. B **67**, 214103 (2003).
- ³⁴ C. Domain, C.S. Becquart and J. Foct, Phys. Rev. B **69**, 144112 (2004).
- ³⁵ C.J. Först, J. Slycke, K.J. Van Vliet and S. Yip, Phys. Rev. Lett. **96**, 175501 (2006).
- ³⁶ T.T. Lau, C.J. Först, Xi Lin, J.D. Gale, S. and K.J. Van Vliet, Phys. Rev. Lett. **98**, 215501 (2007).
- ³⁷ C.-C. Fu, E. Meslin, A. Barbu, F. Willaime and V. Oison, Solid State Phenom. **139**, 157-164 (2008).
- ³⁸ C.A. Wert, Phys. Rev. **79**, 601-605 (1950).
- ³⁹ W.R. Thomas and G.M. Leak, Phil. Mag. (Series 7) **45**, 656-659 (1954).
- ⁴⁰ V.G. Gavriljuk, V.N. Shvanyuk and B.D. Shanina, Acta Materialia **53**, 5017-5024 (2005).
- ⁴¹ V.G. Gavriljuk, B.D. Shanina, V.N. Shvanyuk and S.M. Teus, J. Appl. Phys. **108**, 083723 (2010).
- ⁴² D.W. Boukhvalov, Yu.N. Gornostyrev, M.I. Katsnelson, A.I. Lichtenstein, Phys. Rev. Lett. **99**, 247205 (2007).
- ⁴³ J.A. Slane, C. Wolverton and R. Gibala, Met. Mater. Trans. A **35**, 2239-2245 (2004).
- ⁴⁴ F. Körmann, A. Dick, B. Grabowski, T. Hickel and J. Neugebauer, Phys. Rev. B **85**, 125104 (2012).
- ⁴⁵ G. Miyamoto, J.C. Oh, K. Hono, T. Furuhashi and T. Maki, Acta Materialia **55**, 5027-5038 (2007).
- ⁴⁶ T.P.C. Klaver, P. Olsson and M.W. Finnis, Phys. Rev. B **76**, 214110 (2007).
- ⁴⁷ J.D. Tucker, R. Najafabadi, T.R. Allen and D. Morgan, J. Nucl. Mater. **405**, 216 (2010).
- ⁴⁸ T.P.C. Klaver, D.J. Hepburn and G.J. Ackland, Phys. Rev. B **85**, 174111 (2012).
- ⁴⁹ G. Kresse and J. Hafner, Phys. Rev. B **47**, 558-561 (1993).
- ⁵⁰ G. Kresse and J. Furthmüller, Phys. Rev. B **54**, 11169 (1996).
- ⁵¹ J.P. Perdew *et al.*, Phys. Rev. B **46**, 6671 (1992).
- ⁵² S.H. Vosko, L. Wilk and M. Nusair, J. Can. Phys. **58**, 1200 (1980).
- ⁵³ P.E. Blöchl, Phys. Rev. B **50**, 17953 (1994).
- ⁵⁴ G. Kresse and D. Joubert, Phys. Rev. B **59**, 1758 (1999).
- ⁵⁵ M. Methfessel and A.T. Paxton, Phys. Rev. B **40**, 3616 (1989).
- ⁵⁶ H. Jónsson, G. Mills and K.W. Jacobsen, in *Classical and Quantum Dynamics in Condensed Phase Simulations, Chapter 16*, edited by B.J. Berne, G. Ciccotti and D.F. Coker (World Scientific, 1998), p. 385.
- ⁵⁷ G.J. Ackland and R. Thetford, Phil. Mag. A **56**, 15 (1987).
- ⁵⁸ S.Han, L.A.Zepeda-Ruiz, G.J.Ackland, R.Car and D.J.Srolovitz, J. App. Physics **93**, 3328 (2003).
- ⁵⁹ P. Olsson, T.P.C. Klaver and C. Domain, Phys. Rev. B **81**, 054102 (2010).
- ⁶⁰ N. Juslin and K. Nordlund, J. Nucl. Mater. **382**, 143-146 (2008).
- ⁶¹ P.H. Chen, X.C. Lai, L.Z. Liu, X.L. Wang, B. Bai, B.Y. Ao and Y. Long, J. Nucl. Mater. **405**, 156-159 (2010).
- ⁶² B.D. Butler and J.B. Cohen, Ultramicroscopy **52**, 238-242 (1993); J. Phys. I, **2**, 1059-1065 (1992).
- ⁶³ L. Cheng, A. Böttger, Th.H. de Keijser, E.J. Mittemeijer, Scr. Metal. et Mater. **24**, 509-514 (1990).
- ⁶⁴ A. Dick, F. Körmann, T. Hickel and J. Neugebauer, Phys. Rev. B **84**, 125101 (2011).
- ⁶⁵ M.A. Shumilov, A.P. Kozak, L.I. Yakushechkina and K.N. Sokolov, Zh. Fiz. Khim. **47**, 2169 (1973).
- ⁶⁶ I.A. Abrikosov, A.E. Kissavos, F. Liot, B. Alling, S.I. Simak, O. Peil and A.V. Ruban, Phys. Rev. B **76**, 014434 (2007).
- ⁶⁷ J.A. Lobo and G.H. Geiger, Metal. Trans. A **7**, 1359-1364 (1976).
- ⁶⁸ D.J. Siegel and J.C. Hamilton, Phys. Rev. B **68**, 094105 (2003).
- ⁶⁹ A. Wagner and D.N. Seidman, Phys. Rev. Lett. **42**, 515 (1979).
- ⁷⁰ J. Amano and D.N. Seidman, J. Appl. Phys. **56**, 983 (1984).
- ⁷¹ A.S. Soltan, R. Vassen and P. Jung, J. Appl. Phys. **70**, 793 (1991).
- ⁷² V. Philipps and K. Sonnenberg, J. Nucl. Mater. **114**, 95-97 (1983).
- ⁷³ J.B. Adams and W.G. Wolfer, J. Nucl. Mater. **158**, 25-29 (1988).
- ⁷⁴ A.B. Lidiard, Phil. Mag. (Series 7) **46**, 1218-1237 (1955).
- ⁷⁵ A.D. LeClaire and A.B. Lidiard, Phil. Mag. **1**, 518-527 (1956).
- ⁷⁶ P. Erhart, in *Atomic Defects in Metals*, edited by H. Ullmaier, Landolt-Börnstein New Series III (Springer, Berlin, 1991) **25**, Chapter 2, p. 88.
- ⁷⁷ G. Henkelman, B.P. Uberuaga and H. Jónsson, J. Chem. Phys. **113**, 9901 (2000).
- ⁷⁸ R.P. Smith, Trans. Metall. Soc. AIME **230**, 476 (1964).
- ⁷⁹ J. Ågren, Scripta Metall. **20**, 1507-1510 (1986).
- ⁸⁰ A.D. LeClaire in *Diffusion in Solid Metals and Alloys*, edited by H. Mehrer, Vol **26**, The Landolt-Börnstein Database (Springer Materials), p. 471-503.
- ⁸¹ P. Thibaux, A. Métenier and C. Xhoffer, Metall. and Mater. Trans. A **38**, 1169-1176 (2007).
- ⁸² R. Lappalainen and A. Anttila, Appl. Phys. A **42**, 263-267 (1987).
- ⁸³ G.J. Thomas and R. Bastasz, J. Appl. Phys. **52**, 6426-6428 (1981).
- ⁸⁴ H.K.D.H. Bhadeshia, J. Mater. Sci. **39**, 3949-3955 (2004).
- ⁸⁵ K. Oda, H. Fujimura and H. Ino, J. Phys.:Condens. Matter **6**, 672-692 (1994).
- ⁸⁶ H. Numakura, K. Kashiwazaki, H. Yokoyama and M. Koiwa, J. Alloys Comp. **310**, 344-350 (2000).
- ⁸⁷ T. Sourmail, Mat. Sci. Tech. **17**, 1-14 (2001).

- ⁸⁸ E. H. Megchiche, S. Pérusin, J.-C. Barthelat and C. Mijoule, Phys. Rev. B **74**, 064111 (2006).
- ⁸⁹ E.H. Megchiche, C. Mijoule and M. Amarouche, J. Phys.: Condens. Matter **22**, 485502 (2010).
- ⁹⁰ K. Tapasa, A.V. Barashev, D.J. Bacon and Yu.N. Osetsky, Acta Materialia **55**, 1-11 (2007).
- ⁹¹ G.J. Thomas, W.A. Swansiger and M.I. Baskes, J. Appl. Phys. **50**, 6942 (1979).
- ⁹² R.J.K. Nicholson and J.M. Walls, J. Nucl. Mater. **76-77**, 251 (1978).
- ⁹³ N. Yoshida, E. Kuramoto and K. Kitakijima, J. Nucl. Mater. **103**, 373 (1981).
- ⁹⁴ E. C. Bain, Trans. AIME 70, 25 (1924).